



Cite this: *Energy Environ. Sci.*,  
2015, 8, 1905

Received 19th April 2015,  
Accepted 29th May 2015

DOI: 10.1039/c5ee01215e

[www.rsc.org/ees](http://www.rsc.org/ees)

# Lithium salts for advanced lithium batteries: Li-metal, Li-O<sub>2</sub>, and Li-S

Reza Younesi,<sup>\*ab</sup> Gabriel M. Veith,<sup>c</sup> Patrik Johansson,<sup>†de</sup> Kristina Edström<sup>be</sup> and Tejs Vegge<sup>a</sup>

Presently lithium hexafluorophosphate (LiPF<sub>6</sub>) is the dominant Li-salt used in commercial rechargeable lithium-ion batteries (LIBs) based on a graphite anode and a 3–4 V cathode material. While LiPF<sub>6</sub> is not the ideal Li-salt for every important electrolyte property, it has a uniquely suitable combination of properties (temperature range, passivation, conductivity, etc.) rendering it the overall best Li-salt for LIBs. However, this may not necessarily be true for other types of Li-based batteries. Indeed, next generation batteries, for example lithium-metal (Li-metal), lithium-oxygen (Li-O<sub>2</sub>), and lithium-sulfur (Li-S), require a re-evaluation of Li-salts due to the different electrochemical and chemical reactions and conditions within such cells. This review explores the critical role Li-salts play in ensuring in these batteries viability.

## Broader context

Batteries are one of the most efficient energy storage systems, which in combination with renewable energy sources like solar, wind, and hydro-power can decrease our society's dependence on fossil fuels. Today's rechargeable batteries are, however, far from being fully competitive for large-scale applications such as electric vehicles and grid storage. In order to meet the increasing energy storage/conversion demands in the best possible way, various battery concepts referred to as beyond Li-ion batteries, such as lithium-metal, lithium-oxygen and lithium-sulfur batteries, have been subject to intense research in recent years. These advanced lithium batteries still suffer from issues often associated with the properties of their electrolytes. Indeed, electrolytes based on aprotic solvents and Li-salts commonly used in commercial Li-ion batteries have failed in advanced lithium batteries. Here, we present an overview of the different requirements that Li-salts need to fulfill to be implemented in any lithium batteries, as well as studies investigating their roles in advanced lithium batteries.

## 1. Introduction

The successful integration of solar, wind, and hydro power with energy storage systems like batteries will play a pivotal role in reforming our society from being dependent on fossil fuels to being able to rely more on renewable energy sources.<sup>1,2</sup> A major challenge is to design better batteries for large-scale applications such as electric vehicles (EVs) and grid storage, which will require higher energy and power densities, as well as a

significant reduction in cost.<sup>1,2</sup> In response to this challenge, various “new” lithium battery concepts such as the lithium-metal (Li-metal), lithium-oxygen (Li-O<sub>2</sub>), and lithium-sulfur (Li-S) batteries are now being intensely studied. These “advanced lithium batteries” are still in their early stages of research and all suffer from several obstacles like poor utilization of Li-metal, high cost, safety concerns, capacity fading, complicated chemistries and reactions, etc. as reviewed in several papers.<sup>3–9</sup> A critical parameter for all these battery systems is “the role of the electrolyte”. Coulombic efficiency and dendrite formation of Li-metal as well as the degradation of electrolytes by the intermediate and final reaction products in Li-O<sub>2</sub> and Li-S batteries are directly influenced by the electrolyte.

## 2. Li-salts in aprotic electrolytes

Most electrolytes investigated for rechargeable intercalation batteries and advanced cell chemistries are based on a matrix of aprotic organic solvent(s); other electrolyte concepts like ionic liquids (IL), solids/ceramics, polymers, and aqueous based systems

<sup>a</sup> Department of Energy Conversion and Storage, Technical University of Denmark, Frederiksborgvej 399, P.O. Box 49, DK-4000 Roskilde, Denmark. E-mail: reyo@dtu.dk

<sup>b</sup> Department of Chemistry-Ångström Laboratory, Uppsala University, Box 538, SE-75121 Uppsala, Sweden. E-mail: reza.younesi@kemi.uu.se

<sup>c</sup> Oak Ridge National Laboratory, Materials Science and Technology Division, Oak Ridge, TN 37831, USA

<sup>d</sup> Department of Applied Physics, Chalmers University of Technology, SE-41296 Göteborg, Sweden

<sup>e</sup> ALISTORE-ERI European Research Institute, 33 rue Saint Leu, 80039 Amiens, France

<sup>†</sup> Current address: Visiting Professor at LRCS/CNRS UMR7314, Université de Picardie Jules Verne, 33 rue Saint Leu, 80039 Amiens, France.



are also investigated, but generally have lower ionic conductivities and higher production costs, or lead to batteries with less power density, limiting their utilization.<sup>10–17</sup> ILs and solid/ceramic are still hampered by expensive manufacturing and purification process, which turn them inappropriate for large scale applications in commercial lithium batteries. Similar challenges govern rechargeable aqueous lithium batteries using solid state electrolytes and Li-metal anodes, despite recent works showing promising results.<sup>18–20</sup> As an alternative, full cell rechargeable aqueous lithium batteries using  $\text{Li}_2\text{SO}_4$  and  $\text{LiNO}_3$  salt and metal oxide electrodes can offer cheap and environmental friendly batteries. However, the narrow potential window of aqueous electrolytes, compared to aprotic electrolytes, implies limited energy densities. On the other hand, the high ionic conductivity of aqueous electrolytes (1–2 orders of magnitudes higher than aprotic electrolytes) results in very high power densities.

Aprotic organic solvent based electrolytes for LIBs, allowing for both high energy densities and appreciable power densities, contain at least two components: the solvent matrix and the Li-salt. These components together provide a medium to transfer charge between the electrodes *via* the  $\text{Li}^+$  cations and the counter-anions. While several studies have previously reviewed the impact of the solvent chemistry on the performance of lithium batteries,<sup>10–16</sup> the role of the Li-salts has comparatively gained less attention.<sup>14–16,21–24</sup> A large number of new anions with simple linear or more complex cyclic structures have been synthesized in the last three decades, and the anion chemistry of the salt has been shown to have a large impact on many properties of interest. In general, an electrolyte needs to meet several criteria concurrently to be considered for LIBs, which are comprehensively discussed in ref. 10–16. Below, we specifically address the demands put forth by the “advanced lithium batteries”.

## 2.1. Li-salts for re-chargeable batteries

Early studies on lithium batteries with metal anodes in the 1970–1980's were limited to Li-salts with a few anions like hexafluoroarsenate ( $\text{AsF}_6^-$ ), perchlorate ( $\text{ClO}_4^-$ ), hexafluorophosphate ( $\text{PF}_6^-$ ), tetrafluoroborate ( $\text{BF}_4^-$ ), and trifluoromethanesulfonate or triflate (Tf) ( $\text{CF}_3\text{SO}_3^-$ ). A schematic with the chemical structures of these and several other anions discussed in this work is presented in Fig. 1.<sup>25–28</sup> With the development of LIBs it became clear that  $\text{LiAsF}_6$  and  $\text{LiClO}_4$  were inappropriate for commercial cells, due to safety and toxicity concerns. Similarly, the relatively low conductivities of electrolytes based on  $\text{LiTf}$  made also this salt less popular. Later, with the commercialization of graphite anodes, the  $\text{LiPF}_6$  and  $\text{LiBF}_4$  became the most popular Li-salts as they, together with solvents such as ethylene carbonate (EC), could form a solid electrolyte interphase (SEI) on graphite, making rechargeable lithium batteries commercially viable.<sup>29–34</sup> Ultimately,  $\text{LiPF}_6$  became, and still is, the dominant salt in commercial LIBs. This success is not because  $\text{LiPF}_6$  is considered “the best” salt in all categories. In fact,  $\text{LiPF}_6$  is not the leading salt in any of the properties important for batteries like: ionic conductivity – relatively good,<sup>35</sup> sensitivity to hydrolysis – poor,<sup>36</sup> or thermal stability – poor,<sup>37,38</sup> but its success is due to the ability to

provide the best balance of these and other properties, as well as the formation of a proper SEI on the graphite anode and a protective layer on the aluminum cathode current collector. This is a clear example showing the complexity of the criteria the Li-salt should fulfill with respect to the several different components of a cell. For specific applications, other salts are often competitive, *e.g.*  $\text{LiBF}_4$  has shown to improve the performance of LIBs at high (50–80 °C) and low temperatures (–20 °C),<sup>39–41</sup> but its overall drawback is moderate ionic conductivity in the resulting electrolytes.

Several salts inspired by  $\text{LiPF}_6$  and  $\text{LiBF}_4$  have been synthesized in recent years in an attempt to design salts with improved thermal, ionic or other properties. For example, there was an evolution from anions comprised of ligands around a central atom (*e.g.*  $\text{PF}_6^-$ ,  $\text{ClO}_4^-$ ) to large complex anions *e.g.* bis(trifluoromethanesulfonyl)imide (TFSI or sometimes TFSA)<sup>42</sup> and organic ligand based anions *e.g.* bis(oxalate)borate (BOB).<sup>43</sup> One category of Li-salts comprehensively studied for LIBs contains sulfonyl groups. Triflate is the simplest anion in this family, while imide-based anions with two *x*-fluorosulfonyl (*x* = 1–5) groups like bis(fluorosulfonyl)imide (FSI), TFSI, and bis(perfluoroethanesulfonyl)imide (BETI or sometimes PFSI) have recently attracted more attention.<sup>44–46</sup> The common issue with these anions is the aluminum corrosion by their electrolytes, but a proper electrolyte solvent or additive can be applied to reduce the corrosion.<sup>47</sup> Also, two new Li-salts of this family, lithium-cyclo-difluoromethane-1,1-bis(sulfonyl)imide ( $\text{LiDMSI}$ ) and lithium-cyclo-hexafluoropropane-1,1-bis(sulfonyl)imide ( $\text{LiHPSI}$ ) have been reported to form a stable SEI on a graphite anode and passivate an Al current collector significantly better than  $\text{LiTFSI}$ .<sup>48</sup> Other derivations include compounds combining both a mixture of chemical components for these larger bulk anion components such as tris(pentafluoroethyl)trifluorophosphate (FAP),<sup>36</sup> inspired and derived from  $\text{PF}_6^-$ , a family of perfluoroalkyltrifluoroborates  $\text{C}_n\text{F}_{(2n+1)}\text{BF}_3$  (*n* = 1–4),<sup>49</sup> as alternatives to  $\text{BF}_4^-$ , and lithium difluoro(oxalato)borate ( $\text{LiDFOB}$ ), with its combination of different ligands of fluorine and oxalate.<sup>50</sup>

All aforementioned anions (except  $\text{ClO}_4^-$  and BOB) contain fluorine (F) atoms in their structure, which increases safety concerns. In this regard, BOB and more recent F-free anions such as tetracyanoborate (Bison)<sup>51–54</sup> and dicyanotriazolate (DCTA or sometimes TADC)<sup>54–56</sup> are interesting candidates for LIBs. These examples have distinct and unique advantages, but also suffer from issues that have prevented them from replacing  $\text{LiPF}_6$ . The BOB anion is known to take part in forming interphases on both the anode and cathode to improve cell performance, but  $\text{LiBOB}$  has limited solubility in most aprotic solvents. Bison and DCTA both have high thermal stabilities, but relatively low oxidation potentials and low ionic conductivities of their Li-salt electrolytes. There have been attempts to improve the properties of these salts by adding F-species at the expense of increased safety risks and production costs. Several borate-based anions have been synthesized including bis(fluoromalonato)borate (BFMB) to tune the properties of the BOB anion.<sup>57</sup> Similarly, dicyano-trifluoromethyl-imidazole (TDI) and dicyano-pentafluoroethyl-imidazole (PDI) as well as other imidazole or



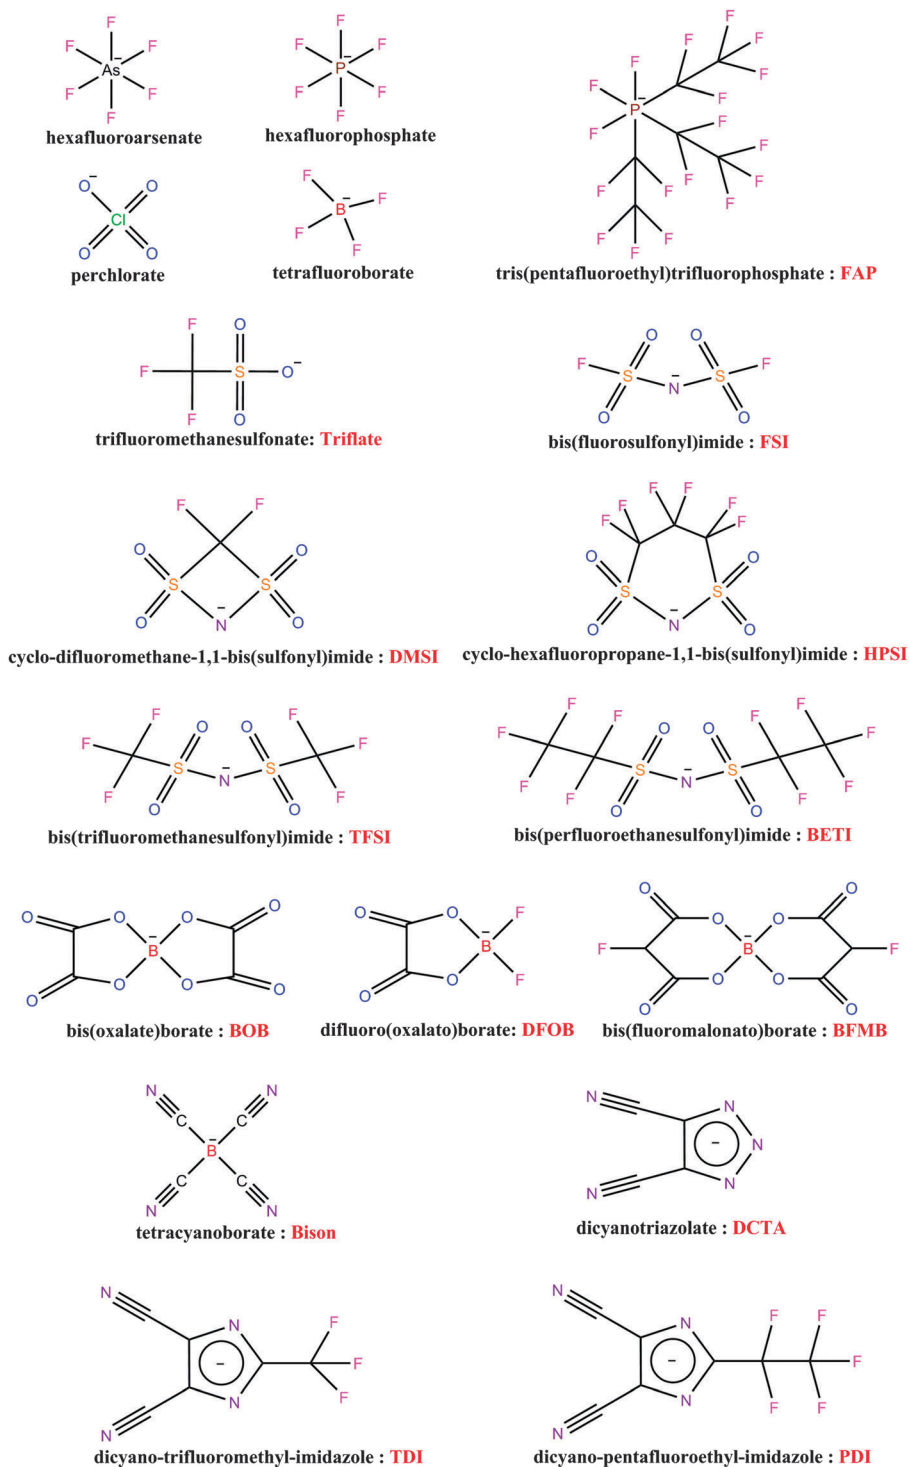


Fig. 1 Chemical structures of several of the anions reviewed.

benzimidazole based anions have shown to be more promising compared to DCTA.<sup>58,59</sup>

Despite the fact that none of the Li-salts mentioned above have been used commercially for LIBs with graphite anodes and 3–4 V cathodes, the “advanced lithium batteries” with different cathode and anode materials may well be better suited.

This review therefore makes a first attempt to reveal how the choice of the Li-salt possibly (or not) can meet the different demands that each of these batteries entails. Below, we therefore step through the basic requirements of electrolytes – pointing out how each of the new concepts differs from LIBs and the role of the Li-salt in this respect.



## 2.2. Solubility

Unlike in protic solvents (*e.g.* water, ammonia, *etc.*) in which anion solvation occurs by hydrogen bond formation, in aprotic (often just quoted as “non-aqueous”) solvents, the absence of acidic protons implies that the dissolution of a Li-salt primarily is by solvent–Li<sup>+</sup> interactions.<sup>15,16</sup> Hence, two steps are involved: the dissociation of Li<sup>+</sup> from the anion, overcoming the lattice energy of the salts, and the consequential formation of coordination bonds between Li<sup>+</sup> and electron lone-pairs of the solvent molecules. Besides the importance of solvent properties like polarity, viscosity, *etc.*, the strength of the Li<sup>+</sup>–anion interaction is critical. Due to this, many simple Li-salts such as LiCl, LiF, Li<sub>2</sub>O, *etc.*, are excluded from electrolyte usage since their strong cation–anion interactions result in high lattice energies and thus poor solubilities in relevant aprotic solvents. Therefore, focus has been on using Li-salts of weakly coordinating anions (WCAs),<sup>60</sup> made through delocalization of the negative charge over the whole anion *via* electron-drawing substituents like –F or –CF<sub>3</sub>, all in order to decrease the Li<sup>+</sup>–anion interaction.<sup>16</sup> Similarly, and to overcome the safety and cost issues, F is now substituted by N in several novel WCAs.<sup>58,61</sup> To explore and screen for new promising Li-salts *ab initio* and DFT calculations have been extensively used to qualitatively address the relative strengths of the Li<sup>+</sup>–anion interaction using isolated ion-pairs and including the WCA chemistry variations above.<sup>62–64</sup> Two recent representative examples using this strategy for distinctly different families of new WCAs aimed at battery usage are the studies by Carboni *et al.*<sup>65</sup> and Scheers *et al.*<sup>66</sup> Given the parameters above, the Li-salt solubility is usually the first consideration when investigating new Li-salts. Moving from LIBs to next generation batteries does not change this notion considerably; the same type of solvents as for LIBs are used and also the preferred salt concentration targets are the same to obtain the maximum conductivity.

## 2.3. Ionic conductivity

Given that next generation batteries with Li–metal anode batteries, including the Li–O<sub>2</sub> and Li–S concepts, in general are proposed for high power application like EVs, any selection of a Li-salt should enable to provide a high Li<sup>+</sup> transport rate.

The Li<sup>+</sup> cation conductivity ( $\sigma_{\text{Li}^+}$ ) originates from both the total ionic conductivity and the cation transference number ( $t_{\text{Li}^+}$ ). Given that the  $t_{\text{Li}^+}$  in non-aqueous solvents is usually smaller than 0.5, the ionic conductivity plays a critical role in the battery performance.<sup>49</sup> In principle, the solvation of a Li-salt in a solvent increases the electrolyte conductivity as a function of salt concentration (by increasing the number of charge carriers). Further increases in Li<sup>+</sup> concentration results in lower ionic mobilities (while still increasing the ionic charge densities, this is outweighed by re-combination of ions to neutral contact ion-pairs). The conductivity of any aprotic Li-salt based electrolyte is, however, dependent not only on the salt concentration, but also the anion, the solvent composition, and the temperature. For example, the conductivity of LiClO<sub>4</sub> in propylene carbonate (PC) reaches a maximum of 1.5 mS cm<sup>–1</sup> at a low salt

**Table 1** An overview of a few selected Li-salts and the ionic conductivities of their electrolytes. All ionic conductivities obtained for 1 M of Li-salt dissolved in 1:1 solvent mixtures (a – volume or b – weight) at 20–25 °C.<sup>14,15,58,70–72</sup>

Li-salt anion	Solvent (mixture)	Ionic conductivity [mS cm <sup>–1</sup> ]
ClO <sub>4</sub> <sup>–</sup>	EC–DMC <sup>a</sup>	10.1
	DME–DOL <sup>a</sup>	7
	TEGDME–DOL <sup>a</sup>	5
AsF <sub>6</sub> <sup>–</sup>	EC–DMC <sup>b</sup>	11.1
PF <sub>6</sub> <sup>–</sup>	EC–DMC <sup>b</sup>	10.8
BF <sub>4</sub> <sup>–</sup>	EC–DMC <sup>b</sup>	4.9
Triflate	EC–DMC <sup>a</sup>	3.1
	DME–DOL <sup>a</sup>	2
TFSI	EC–DMC <sup>b</sup>	9
	DME–DOL <sup>a</sup>	11
	TEGDME–DOL <sup>a</sup>	7
BETI	DME–DOL <sup>b</sup>	11.1
BOB	DME	14.9
DCTA	EC–DMC <sup>b</sup>	2.7
TDI	EC–DMC <sup>b</sup>	6.7
PDI	EC–DMC <sup>b</sup>	6.3

EC: ethylene carbonate; DMC: dimethyl carbonate; DME: 1,2-dimethoxyethane or “monoglyme” or “G1”; DOL: 1,3-dioxolane; TEGDME: tetraethylene glycol dimethyl ether or “tetraglyme” or “G4”.

concentration of 0.08 M, while any further concentration increase results in a lower conductivity.<sup>67</sup> In stark contrast, using a solvent mixture of PC and EC, the highest conductivity, 15 mS cm<sup>–1</sup>, is achieved at a salt concentration of 1 M.<sup>67</sup>

It is commonly assumed in the LIB literature that a 1 M salt concentration provides the highest conductivity, and thus, the focus has been mainly on the composition of solvent mixture. Table 1 shows the ionic conductivity of a few selected Li-salts dissolved in some typical electrolyte solvents/solvent combinations. It should be noted that the measure of total ionic conductivity is most often used as a screening criterion for electrolytes, without considering the more relevant contribution of the lithium ion part of the conductivity,  $\sigma_{\text{Li}^+}$ .

A novel approach recently proposed is to use highly concentrated or “solvent-in-salt” electrolytes, in which the Li-salt is the dominant component, and surprisingly large  $t_{\text{Li}^+}$  are achieved.<sup>68,69</sup> The higher salt concentration means a higher electrolyte cost, but the approach opens new possibilities to overcome electrolyte degradation, especially interesting for Li–O<sub>2</sub> and Li–S batteries, since the solubility and reaction path of intermediate species in these batteries may be tuned by the salt concentration. Also, the cycling efficiency of Li–metal has shown to increase in highly concentrated electrolytes.<sup>68,69</sup>

## 2.4. Donor number (DN)

For any type of battery electrolytes the Gutmann<sup>73</sup> donor number (DN) is an often used measure for solvents; depicting the electron



**Table 2** The DN of different anions, measured using tetrabutylammonium (TBA<sup>+</sup>) as the counter cation<sup>78</sup>


Anion	DN
PF <sub>6</sub> <sup>−</sup>	2.5
AsF <sub>6</sub> <sup>−</sup>	2.5
TFSI	5.4
BF <sub>4</sub> <sup>−</sup>	6.0
ClO <sub>4</sub> <sup>−</sup>	8.4
Tf	16.9

donating properties and hence the ability to interact with acceptors such as protons, Li<sup>+</sup>, and other cations. The higher DN, the higher basicity of the solvent, resulting in strong interaction with hard Lewis acids such as Li<sup>+</sup>. While the DN of Li-salts seldom is mentioned, as most anions have similar and relatively small DN, there is a notable exception of Tf with its rather high DN (Table 2).

Especially in Li–O<sub>2</sub> batteries the role of the DN have recently been highlighted,<sup>74–76</sup> revealing its influence on solubility and life-time of superoxide (O<sub>2</sub><sup>−</sup>) as well as the discharge reaction pathway and the final capacity of the cells. Altering the Li-salt using anions with low DN (*e.g.* PF<sub>6</sub><sup>−</sup> or TFSI) may not have any crucial impact based on the DN, but using LiTf thus might.<sup>76</sup> In Li–S battery electrolytes the DN is an important parameter in controlling the solubility of polysulfide species,<sup>77</sup> even if more studies on this aspect are needed, and also here LiTf is a popular electrolyte salt.

## 2.5. Electrochemical stability window (ESW) and SEI

From a thermodynamic stability standpoint, a battery should contain an electrolyte with the ESW located beyond the reduction and oxidation potential window of the anode and the cathode, respectively. The difference between the lowest unoccupied molecular orbital (LUMO) and the highest occupied molecular orbital (HOMO) of the electrolyte defines the theoretical ESW, which is influenced by the chemistry of both solvent and Li-salt.<sup>15</sup> These properties can easily be computed using DFT approaches for different choices of anions, often WCAs, focusing on the inherent stability *vs.* oxidation<sup>79,80</sup> – giving a screening of the thermodynamic limit to some appreciable accuracy. However, the commercialization of LIBs in the 1990's was launched for cells with alkyl carbonate electrolytes, which are thermodynamically unstable in contact with graphite anodes. The success of graphite anodes relies on the formation of a passivation layer called the solid electrolyte interphase (SEI), which acts as a barrier for electron transfer between the anode and the electrolyte resulting in kinetic stability of the cell and prevents exfoliation during cycling from solvent intercalation. The SEI forms by decomposition of the electrolyte, and thus, the chemistry of electrolyte solvents and salts affects the composition and properties of the SEI. A similar concept is considered for cathodes with the electrochemical potential below HOMO of electrolyte, where

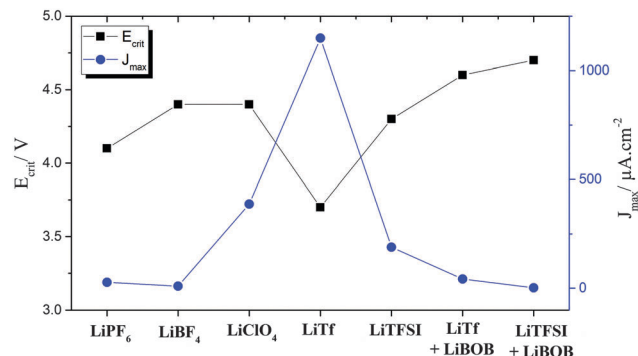

**Fig. 2** Critical corrosion potentials and maximum corrosion current densities observed on Al electrodes in electrolytes containing different Li-salts. Total concentration of salts was 0.5 mol Li-salt in 1 kg of electrolyte mixture of PC and DMMA-TFSA. LiBOB concentration was 0.15 mol kg<sup>−1</sup>. Data obtained from ref. 83.

decomposition of the electrolyte can form cathode/electrolyte passivation layer often called the solid permeable interphase (SPI).<sup>81</sup> Aluminum is commonly used as the cathode current collector due to its low price and the anodic (oxidative) decomposition of the electrolyte resulting in the formation of a passivation layer on the aluminum, suppressing corrosion in the following cycles.<sup>82</sup> Fig. 2 shows the influence of different anions on the corrosion potential and maximum corrosion current density of aluminum electrodes in electrolytes containing Li-salt dissolved in propylene carbonate and *N,N*-diethyl-*N*-methyl-*N*-(2-methoxyethyl)-ammonium bis(trifluoromethyl-sulfonyl)azanide (PC and DMMA-TFSA).<sup>83</sup>

The potential of lithium (−3.04 *vs.* the standard hydrogen electrode) is higher than the LUMO of aprotic electrolytes, which usually results in the continuous decomposition of electrolyte unless a proper SEI protects the electrolyte – and as all the next generation batteries considered here use Li-metal anodes, this must be considered carefully. In contrast, on the cathode side of Li–O<sub>2</sub> and Li–S batteries, the anodic decomposition of electrolytes should be less of an issue as the thermodynamic potentials of cell reactions are below ~3 V *vs.* Li<sup>+</sup>/Li<sup>0</sup>, which is within the ESW of most aprotic electrolytes. However, overpotentials originating from poor conductivity of reaction products (particularly in Li–O<sub>2</sub> cells) can potentially increase the potential of the charging reactions, leading to a higher risk of anodic decomposition.

## 2.6. Thermal stabilities

It is well known that LiPF<sub>6</sub> has poor thermal stability due to the weak P–F bond and the auto-decomposition reaction of PF<sub>6</sub><sup>−</sup> = >PF<sub>5</sub> + F<sup>−</sup>, which can result in formation of toxic gaseous, HF and several other decomposition products, even at moderately high temperatures.<sup>84</sup> The strategies to overcome this issue can be divided to 3 categories: (i) replacing LiPF<sub>6</sub> by Li-salts with higher thermal stabilities, (ii) using a co-salt to improve the thermal stability of LiPF<sub>6</sub>-based cells, (iii) adding additives to increase the thermal safety of LiPF<sub>6</sub>-based cells. The first two approaches have initiated several works to synthesise





**Table 3** Melting points and initial decomposition temperatures of Li-salts as measured by thermogravimetric analysis

Salt	Melting point [°C]	Initial decomposition temperature [°C]
LiPF <sub>6</sub>	200 <sup>a</sup>	125 <sup>b</sup>
LiBF <sub>4</sub>	293–300 <sup>a</sup>	175 <sup>b</sup>
LiClO <sub>4</sub>	236 <sup>a</sup>	
LiBOB	> 300 <sup>a</sup>	275 <sup>b</sup>
LiFSI	135 <sup>c</sup>	200 <sup>c</sup>
LiTFSI	234 <sup>d</sup>	360 <sup>e</sup>
LiTf	~ 420 <sup>f</sup>	
LiDFOB	265–271 <sup>a</sup>	200 <sup>b</sup>

<sup>a</sup> Ref. 91. <sup>b</sup> Ref. 92. <sup>c</sup> Ref. 93. <sup>d</sup> Ref. 94. <sup>e</sup> Ref. 21. <sup>f</sup> Ref. 15.

e.g. sulfone- and boron-based anions with higher thermal stabilities.<sup>85</sup> Table 3 shows the melting points and initial decomposition temperatures of several Li-salts. However, the thermal stability of the Li-salt is not necessarily an adequate measure to improve the thermal stability of batteries. In fact, the solvent chemistry as well as the electrode composition and morphology together with the Li-salt all influence the thermal stability of the cells. For example, LiBOB, as compared to LiPF<sub>6</sub>, has been shown to decrease the reactivity of mesocarbon microbeads negative electrodes, while it increases the reactivity with the LiCoO<sub>2</sub> positive electrode.<sup>86</sup> The graphite electrode has a higher thermal stability in an LiPF<sub>6</sub> EC/DMC electrolyte compared to an identical cell with the LiBF<sub>4</sub> salt, even though the LiPF<sub>6</sub> salt has lower decomposition temperature as compared to LiBF<sub>4</sub>.<sup>29</sup> Such studies have been mainly performed for Li-ion batteries with electrolytes and electrodes close to commercial cells, and Li-metal electrodes have rarely been the subject of these thermal stability investigations.<sup>87–90</sup> The introduction of novel anions showing promising results for Li-metal anodes thus requires a new look at the thermal stability, while the challenge to meet several other requirements in addition to the thermal stability of course remains.

### 2.7. Chemical stability in contact with reaction products

Electrolytes should be either (i) thermodynamically stable or (ii) kinetically stabilized in contact with battery components including electrodes, as discussed above. Likewise, electrolytes should be stable in contact with reaction products formed during cycling. This is particularly important for the Li-O<sub>2</sub> and Li-S concepts in which new species are formed in each cycle, in contrast to conventional LIBs based on intercalation electrodes.

It should be emphasized that the degradation of Li-salts (or solvents) by intermediate/final products in Li-O<sub>2</sub> and Li-S batteries are not to be confused with the concept of partial decomposition of Li-salts on the anode and cathode surfaces in LIBs to form the SEI and/or protective layers on the anode and/or the current collectors (see above). In contrast, in Li-O<sub>2</sub>

batteries the intermediate/final products continuously form in each discharge and consequently even a very small amount of electrolyte degradation make for pre-mature battery failure (which is observed today).

A most noteworthy contamination in batteries is traces of water and the hydrolytic sensitivity most Li-salt anions demand special care to be taken. This basically means extra costs for the extreme purification of electrolyte salts and solvents as well as for assembling cells in water-free environments. More importantly, the hydrolysis of the F-containing anions is often accompanied with HF formation, which is a serious safety issue. HF can also degrade electrolytes and electrode materials, especially at high temperatures or high voltages.

PF<sub>6</sub> is well known to be poor in terms of hydrolysis as it can readily degrade to phosphorus pentafluoride (PF<sub>5</sub>) and lithium fluoride (LiF), and the former can easily undergo hydrolysis to form hydrofluoric acid (HF).<sup>95</sup> Hence, commercial LIBs usually contain a mixture of scavengers, at the expense of extra cost, to adsorb produced HF. Under some circumstances HF is actually believed to play key role in formation of a flexible SEI on Li-metal, which can increase cycling efficiency of the electrode (see Section 4).

For Li-O<sub>2</sub> and Li-S batteries, the role and influence of any contaminant water in the reaction pathways and the formation of reaction products are under debate.<sup>75,96,97</sup> This is notably critical to assess for the Li-O<sub>2</sub> concept as these cells are open to the surrounding atmosphere, and thus the Li-salt should remain robust in contact with traces of water originating also from any “pure” oxygen feed.

### 2.8. Production cost of Li-salt

The final cost of any Li-salt depends on several parameters such as cost and toxicity of reagents, synthesis procedure, waste produced, the salt purification, *etc.* Also, the scalability of the process(es) and the intellectual property rights will eventually influence the cost. Notably, large efforts have been devoted to develop low-cost and scalable methods to synthesize LiPF<sub>6</sub> with a very high purity. In early works, LiF and PF<sub>5</sub> were reacted in liquid anhydrous hydrogen fluoride or in an organic solvent such diethyl ether.<sup>98,99</sup> However, H<sub>2</sub>O and HF are two common impurities resulting and requires further purification of LiPF<sub>6</sub> by recrystallization in a dry organic media. Later, a method developed by Wiesboeck *et al.*, LiF and PF<sub>5</sub> were reacted in the presence of acetonitrile at high pressure and low temperatures (–40 to –80 °C) to form a tetra-acetonitrolo lithium hexafluorophosphate, Li(CH<sub>3</sub>CN)<sub>4</sub>PF<sub>6</sub>, complex, to be dissociated into very high purity LiPF<sub>6</sub> and CH<sub>3</sub>CN.<sup>100</sup> Similarly Li(CH<sub>3</sub>CN)<sub>4</sub>PF<sub>6</sub> can also be produced by a direct reaction between a HPF<sub>6</sub> acid solution and LiOH in acetonitrile.<sup>101</sup> The general trend is to improve the synthesis methods and production time, by simplifying the procedure while increasing the purity of the produced LiPF<sub>6</sub>.<sup>102–106</sup>

To our knowledge, there is no report discussing all synthesis procedures for the different Li-salts. Since many of the Li-salts have only been synthesized in a small scale with different purities within academia and with no available information



Table 4 Estimated prices of common battery Li-salts and their molecular weight

Salt	Molecular weight [g mol <sup>-1</sup> ]	Sigma-Aldrich		BASF		EMD Millipore
		Estimated price <sup>a</sup> [USD per kg]	Purity (%)	Price <sup>b</sup> [USD per kg]	Purity (%)	Estimated price <sup>a</sup> [USD per kg]
LiPF <sub>6</sub>	151.9	8700	≥ 99.99	500	99.8	
LiBF <sub>4</sub>	93.7	28 000	99.99	650	97.5	5800
LiAsF <sub>6</sub>	195.9	15 000	98	—	—	
LiClO <sub>4</sub>	106.4	2700	99.99	500	99.0	
LiBOB	193.8	5200	—	650	99.0	
LiTf	156	8000	99.995	650	99.5	
LiTFSI	287.1	4100	99.95	650	99.9	3800
LiDFOB	143.8	9500	99	—	—	

<sup>a</sup> The prices are estimated according to the available prices in the website of Sigma-Aldrich and EMD Millipore for small quantities of 10–250 g in March–April 2015. <sup>b</sup> The prices are obtained from BASF for 1 kg of the salts in March–April 2015.

about the expenses of the synthesis process, it is impossible to truly compare the total cost for the large scale production of different salts. The purchase price of commercialized Li-salts may, however, give a reasonable first approximation comparison and in Table 4 we report these data based on three different providers. Note that to obtain a 1 M electrolyte using heavier (higher molecular weight) salt requires more mass of the salt, resulting higher cost and lower gravimetric energy density of cells, and hence also the molecular weight of the Li-salt needs to be accounted for (*e.g.* to prepare 1 M electrolyte using the LiTFSI salt compared to the LiBF<sub>4</sub> salt, almost 3 times more in mass is needed). The large cost differences are likely due to the different purities of the Li-salts; for example Sigma-Aldrich provides “battery grade” Li-salts, usually with a purity above 99.99%, while the salts produced by BASF have lower purities (no comparative information is provided by EMD Millipore).

The cost of the Li-salt is, however, not yet a limiting factor for neither Li-metal, Li–O<sub>2</sub>, or Li–S batteries, since these are still in their early development and it is difficult to predict the Li-salt ultimately to be implemented in commercial cells.

### 3. Applying current knowledge to future battery chemistries

In Section 2, many of the important criteria used to evaluate Li-salts for Li-ion batteries were discussed. These criteria (solubility, conductivity, stability, SEI formation) are likely to also be critical for future Li-based rechargeable batteries. However, with these newer chemistries other factors also become important. For example, in metal–air batteries, the electrolyte needs to be stable in contact with O<sub>2</sub> and its reduced species. The next three sections discuss the role of the Li-salt in Li-metal, Li–O<sub>2</sub> and Li–S batteries with a particular emphasis on the differences in reaction chemistry of these systems as compared to the LIB's. There is still no complete predictive insight allowing rational pre-selection of a specific Li-salt for

specific battery chemistries. With this in mind, the status of the many different Li-salt selections for tests made for each of the three next generation batteries is reviewed below.

### 4. Li-salts for Li–metal batteries

In theory, Li-metal is the best anode material for any lithium-based battery technologies. It has a high volumetric energy density (2046 mA h cm<sup>-3</sup>) and the highest gravimetric energy density (3862 mA h g<sup>-1</sup>) of any known material.<sup>107</sup> It also has a flat voltage profile and the lowest redox potential (–3.04 V *vs.* SHE) of any alkali metal. As is commonly known in the LIB field, however, metallic Li electrodes suffer from two fatal flaws. First, metallic Li is prone to form dendrites during cycling, which increases the risk of catastrophic fires or loss of capacity when the dendrites separate from the bulk of the Li.<sup>108</sup> Second, Li electrodes continuously form a SEI layer with cycling, causing significant Coulombic efficiency losses, consumption of Li, and increases in cell resistance.<sup>108</sup> This effect is often evident in studies using Li-based half-cells such as the data shown in Fig. 3. Here, the same batch of LiNi<sub>1/3</sub>Mn<sub>1/3</sub>Co<sub>1/3</sub>O<sub>2</sub> cathode is cycled *versus* graphite (full cell) or a Li-metal anode (half-cell). For the half-cell there is an apparent loss of capacity at *ca.* 60 cycles due to the insulating SEI layer being formed. These two problems need to be solved because the use of a Li-metal anode is required for advanced battery chemistries like Li–O<sub>2</sub> and Li–S in order to realize dramatic improvements in energy density, vehicle range, and cost requirements envisioned.

There are two general methods to prevent these losses for Li-metal anodes. First, one could introduce a solid electrolyte to act as a physical barrier.<sup>109</sup> This barrier should be strong enough to prevent dendrites from pushing towards the cathode while simultaneously preventing liquid electrolyte from coming in contact with the metallic Li thus preventing SEI formation. Modelling performed by Monroe and Newman indicated that the lithium dendrite formation can be inhibited when the solid



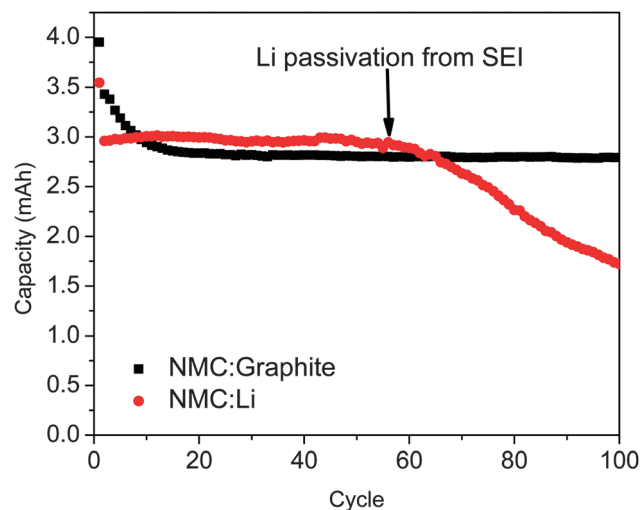


Fig. 3 Capacity versus cycle number measured for  $\text{LiNi}_{1/3}\text{Mn}_{1/3}\text{Co}_{1/3}\text{O}_2$  (NMC) versus Li-metal (●) and graphite (■) using a standard 1.2 M  $\text{LiPF}_6$  in EC/DMC (3:7 wt%) electrolyte at 20 °C. The capacity fade at ~60 cycles for the Li anode is due to SEI formation.

electrolytes shear modulus is twice that of metallic Li, or greater than about 7 GPa at room temperature.<sup>110,111</sup> The potential choices of solid electrolytes are limited due to instability in contact with Li-metal and low ionic conductivities,<sup>112</sup> however, under the right conditions, lithium can be cycled thousands of times with very little loss of capacity.<sup>113,114</sup> Advances in protected Li-anodes will require significant research on the solid-solid interface, formation of thin ceramic sheets, and optimization of electrolyte chemistries. The second method to stabilize Li-metal anodes is through a protective layer formed by a chemical reaction. An SEI layer would fall into this category as well as a flexible polymeric material.<sup>115</sup>

Attempts to develop electrolyte chemistries to stabilize the Li-metal surface have been performed for a long time. In all cases, the solvent and the Li-salt decompose to form an SEI layer. The anions of the Li-salts are decomposed forming the inorganic component of the SEI layer as has been widely discussed.<sup>108</sup> No predictive correlation between the choices of Li-salts and solvents and the best SEI exists, despite the relatively low number of suitable battery Li-salts. In some cases, like LiBOB, the SEI layer is too thick and highly resistive, which lowers the power and rate performance of the cell.<sup>116</sup> Other salts such as  $\text{LiBF}_4$  do not form stable dense SEI layers on Li, however thinner SEI layers built using  $\text{LiBF}_4$  do result in a low charge transfer resistances enabling operations at low temperatures and high rates.<sup>116</sup> In yet other cases, the reduction of the anion is not sufficient to form a suitable SEI layer to prevent the continuous consumption of the electrolyte. The desire is to develop the optimal chemistry that will be compatible with Li-metal as well as current state-of-the-art high voltage cathode materials. There have been hundreds of studies that have focused on understanding the origin of the SEI layer on Li-metal as a function of solvent mixed with a salt. Here, we only intent to highlight key findings on Li-metal-SEI chemistry and point out

what we believe are the most promising research directions or particularly interesting results.

For the passivation of Li-metal anodes there are only a few solvent/salt systems which produce a stable SEI that can enable long term cycling.<sup>14</sup> A commonality to these solvent/salt systems is that they are not purely based on carbonates/ $\text{LiPF}_6$ , in contrary to electrolytes for commercial LIBs. For example, electrolytes of DOL and  $\text{LiClO}_4$  or  $\text{LiAsF}_6$  provide excellent Li passivation resulting in cycling efficiencies greater than 96–98%.<sup>117</sup> The lithium deposition is smooth and results in very little dendrite formation. The origin of this stability is the polymerization of DOL, which forms an elastic barrier on the Li surface that “breathes” as the surface undergoes volume changes.<sup>108,118</sup> This system suffers when the electrolyte gets consumed during high rate applications and tends to form smaller Li particles.<sup>117</sup> These smaller Li particles are then passivated which consumes all available electrolyte within the cell. A second stable system is 2-methyltetrahydrofuran (2-MeTHF) with  $\text{LiAsF}_6$ , which cycles with >96% efficiency. It is believed that the 2-MeTHF provides a good surface because it reacts very slowly with the Li-metal.<sup>119</sup> Finally, the LiBETI salt has been reported to cycle Li with around 97% efficiency in a EC-DME solvent mixture.<sup>120</sup>

The results above have led to a search for other potential electrolyte chemistries, with the gained knowledge that cyclic oxygen containing solvent molecules and an inorganic salt capable of forming LiF appear to be essential for a dense and stable SEI layer. Indeed, nearly all the Li-salts under investigation, with the exception of  $\text{LiClO}_4$  and LiBOB, are fluorinated. Fluorinated salts tend to be more hygroscopic and thus contain some more water (ppms), which changes the SEI chemistry significantly.

One of the most interesting sets of studies to correlate chemical reactivity of electrolyte components with Li passivation was reported by Odziemkowski and Irish.<sup>121,122</sup> These authors measured the magnitude and rate of reaction of mixtures of several salts ( $\text{LiAsF}_6$ ,  $\text{LiClO}_4$ ,  $\text{LiBF}_4$ ,  $\text{LiPF}_6$  and  $\text{LiN}(\text{CF}_3\text{SO}_2)_2$ ) with various solvents (THF, 2-MeTHF and PC) in contact with pure Li-metal. They found the  $\text{LiAsF}_6$  salt to react most rapidly with Li, forming a passivating film.<sup>121,122</sup> This explains the suitability of  $\text{LiAsF}_6$  to form a stable SEI layer. The other salts react slower and take longer to form a passivating film. With these slower reacting salts,  $\text{LiPF}_6$  and  $\text{LiBF}_4$  had the largest reactivity, as indicated with the largest corrosion potential maxima. This data shows that reduction of the salt anion may be most critical to the passivation of Li. The influence of the solvent was not as dramatic, although there was clear evidence that solvent plays a role in the stability, especially with time. Subsequent studies by Rahner showed that the reactivity of the salts depended strongly on the solvent properties and salt concentrations.<sup>123</sup> Indeed, at low salt concentrations of  $\text{LiClO}_4$ , the anion reduction and PC decomposition is faster than at high concentrations of  $\text{LiClO}_4$ . This correlation between the Li-salt and solvent indicates there is a possibility to optimize the formation chemistry of the SEI layer although this chemistry maybe far from optimal for battery operation.

To understand some of the effects of salts on the SEI formation Nishikawa *et al.* have performed holographic interferometry measurements to measure the concentration of gradients of  $\text{Li}^+$





as a function of potential and time near dendrites and a Li surface in PC with  $\text{LiClO}_4$  and  $\text{LiPF}_6$ .<sup>124</sup> Their results show an incubation period, which depends on the salt and the applied potential, which mediates dendrite growth and roughness. For example at low potentials ( $0.5 \text{ mA cm}^{-2}$ ), the concentration of  $\text{Li}^+$  around a Li-dendrite was the same as the concentration of Li around a dendrite free surface until about 25 seconds. At this point, the concentration of  $\text{Li}^+$  dropped significantly as the dendrite grew. Interestingly, the incubation period around the dendrite in  $\text{LiPF}_6$  based electrolytes was longer than the period for  $\text{LiClO}_4$  based electrolytes at a current density of  $0.5 \text{ mA cm}^{-2}$ . At higher applied currents ( $>1.0 \text{ mA cm}^{-2}$ ), the incubation period is reversed such that  $\text{LiClO}_4$  reacts faster. The authors attribute these changes in incubation periods to SEI formation and electrolyte impurities.<sup>124</sup> Within  $\text{LiPF}_6$  electrolytes, there is a small concentration of water, which reacts with  $\text{LiPF}_6$  to form small concentrations of HF. This HF reacts with the Li-metal to form a dense LiF surface.  $\text{LiClO}_4$  does not suffer from the same reactions with water so there are less inorganic salts on the Li-metal surface. With the application of a potential, the less passivated Li surface ( $\text{LiClO}_4/\text{PC}$ ) will rapidly react to form dendrites, whereas the LiF terminated surface requires more current to break up the LiF surface leading to longer incubation times. At higher rates, there is not enough time for the HF to diffuse and react with the Li surface leading to lower incubation times. Interestingly, the longer incubation times needed to break down the LiF layer would be consistent with the widely reported smoother lithium deposits using  $\text{LiPF}_6$  salts compared to  $\text{LiClO}_4$ . Electrochemical quartz crystal microbalance measurements (EQCM) support the more stable, or thinner, SEI produced with  $\text{LiPF}_6$  compared to  $\text{LiClO}_4$  and other salts such as  $\text{LiTf}$  consistent with the arguments laid out above.<sup>125</sup> Subsequent work by Nishikawa *et al.* found the SEI layer to affect the morphology and growth rates of the Li dendrites. They reported that  $\text{LiPF}_6$  dendrites were more hemispherical, while  $\text{LiClO}_4$  dendrites were more like whiskers. The dendrites grow linearly with square root of time, which indicates an ionic mass transfer rate in solution. These results clearly show the importance of ionic conductivity in the electrolyte, which is a function of Li-salt species.<sup>126</sup> Larger anions are less mobile in solution and tend to have higher Li-dissociation constants. Under circumstances where Li dendrites are formed, this higher Li transfer may accelerate dendrite formation.<sup>14</sup>

Throughout all the studies of Li-metal electrodes, the most common salt used is  $\text{LiPF}_6$ . Regardless,  $\text{LiPF}_6$  does not successfully passivate metallic Li surfaces or enable extended cycling of Li. Consequently, there has recently been a desire to discover new Li-salts, which may form a stable SEI through the formation of more “flexible” decomposition products. These new salts can be broken down into a few categories. The first are based on borate structures. The simplest borate structure is  $\text{LiBOB}$ , Fig. 1, which very effectively forms an SEI layer. Unfortunately, the layer is too resistive to be suitable for extended cycling at high rates and the solubility of  $\text{LiBOB}$  is too low (0.8 M in PC/EC/EMC in 1:1:3 wt%).<sup>116</sup> However, the ability of the BOB anion to polymerize into an extended network presents an opportunity to formulate a more flexible SEI layer, provided the right salt

chemistry can be obtained. Numerous fluorinated borate based salts have been fabricated including  $\text{LiBFMB}$ <sup>57,127</sup> and  $\text{LiDFOB}$ .<sup>50,116,128</sup> Both of these Li salts have much higher solubility in carbonate solvents than  $\text{LiBOB}$  and Li transference numbers greater than  $\text{LiPF}_6$  ( $t_{\text{Li}^+} = 0.47$   $\text{LiBFMB}$ ; 0.33  $\text{LiDFOB}$ ; 0.24  $\text{LiPF}_6$ ).<sup>127</sup> Schedlbauer *et al.* reported a study of the cyclability of Li in  $\text{LiPF}_6$  and  $\text{LiDFOB}$  electrolytes,<sup>129</sup> and found that the  $\text{LiDFOB}$  electrolytes had much higher Coulombic efficiencies compared to  $\text{LiPF}_6$  upon cycling, 95–97% vs. 75% after 500 cycles. Subsequent work by Schedlbauer *et al.* revealed that the  $\text{LiDFOB}$  salt improves cycling efficiencies at a variety of cycling rates ( $0.1\text{--}1.0 \text{ mA cm}^{-2}$ ).<sup>130</sup> These results demonstrate a significant improvement in cyclability and promising potential, though still not on par with graphite electrodes. A second class of designer Li-salts are based on imide chemistry.<sup>48</sup> Two new salts with a ring structure,  $\text{LiDMSI}$  and  $\text{LiHPSI}$ ,<sup>48</sup> are built from the  $\text{LiTFSI}$  structure, but have added or removed F atoms to form a strained ring structure. To our knowledge, there are no reports on the compatibilities with Li-metal.

In addition to designing new Li-salts, there have been several reports of the addition of simple Li-salts to Li-metal surfaces and a corresponding increase in cyclability. For example, Li terminated with  $\text{Li}_3\text{N}$  was shown to cycle with about 85% Coulombic efficiency compared to unterminated Li (70% efficiency) in the same  $\text{LiPF}_6$  based electrolyte.<sup>131</sup> The  $\text{Li}_3\text{N}$  appears to promote the formation of a more complete SEI layer lowering parasitic currents while simultaneously reducing Li transport resistances by almost 50%. Similar to  $\text{Li}_3\text{N}$ , terminating the Li surface with  $\text{Li}_2\text{CO}_3$  also shows an almost 5-fold decrease in diffusion resistances compared to uncoated electrodes after 7 cycles in  $\text{LiPF}_6$  electrolytes.<sup>132</sup> It was recently demonstrated that the addition of  $\text{LiNO}_3$  stabilizes a Li-metal anode during operation in a Li-air cell.<sup>133,134</sup> These authors reported the  $\text{LiNO}_3$  reacts with or inhibits the formation of species that are electrochemically active above 3.4 V (vs.  $\text{Li/Li}^+$ ). The  $\text{LiNO}_3$  also enables cycling of the Li-metal in an oxygen rich environment without excessive SEI formation.<sup>133</sup> It has also been shown that  $\text{O}_2$  gas can stabilize SEI on Li-metal anode leading to increase in Coulombic efficiency in a solution of  $\text{LiClO}_4$  in dimethyl sulfoxide<sup>134</sup> or  $\text{LiTFSI}$  in *N,N*-dimethylacetamide.<sup>135</sup> Finally, it was recently reported that the addition of 0.05 M  $\text{CsPF}_6$  to a  $\text{LiPF}_6/\text{PC}$  electrolyte effectively reduces dendrite formation with cycling.<sup>136</sup> Albeit, the efficiency of the cycled Li is not much better than the standard electrolyte (76.5 vs. 76.6%).<sup>136</sup> The ability to prevent dendrites is a major accomplishment and advancement for the production of safer Li-ion battery cells.

All of the examples described above involve electrolyte chemistries with salt concentrations around 1 M. Several research groups have begun focusing on electrolytes with salt concentrations significantly higher than standard electrolytes. For example, comparing a  $3.27 \text{ mol kg}^{-1}$   $\text{LiBETI}$  to a  $1.28 \text{ mol kg}^{-1}$   $\text{LiBETI}$  solution in PC revealed a significant enhancement in Li-metal cyclability.<sup>68</sup> Indeed, the efficiency increased to nearly 80% after 40 cycles at high salt concentrations, while it dropped to 0 at low concentrations. From TEM data, the authors showed a thinner SEI layer with the higher  $\text{LiBETI}$  concentrations and a thicker SEI layer with lower  $\text{LiBETI}$  concentrations (20 vs. 25 nm). In addition,



the thinner SEI suppresses dendrite formation. The authors believe the solvation of the Li ions is changed sufficiently to modify the SEI formation reaction. Recently, Zhang *et al.* showed that a high Coulombic efficiency of 98.4% could be achieved for >1000 cycles of lithium plating/stripping at a current density of  $4 \text{ mA cm}^{-2}$  when the concentration of LiFSI in DME was increased to 4 M. The average Coulombic efficiency over 500 cycles could be increased to 99.1% at a lower current density of  $0.2 \text{ mA cm}^{-2}$ . These high Coulombic efficiencies are referred to limited side reactions of DME with Li-metal due to the increased concentration of Li-salt as well as to the formation of a highly compact SEI.<sup>137</sup> In another example, Yamada *et al.* recently reported that a supersaturated 4.2 M LiTFSI acetonitrile solution showed a significant increase in stability and cyclability of a graphite anode compared to a traditional 1 M solution.<sup>138</sup> The origin of this stability is likely due to changes in the  $\text{Li}^+$  ion solvation. This is significant because acetonitrile is typically reduced by Li, but these high salt concentrations seem to prevent/reduce the solvent decomposition. In these reports, the reversibility was not as high as desired, but significant improvements were observed.

## 5. Li-salts for Li–O<sub>2</sub> batteries

The Li–O<sub>2</sub> battery, often called the Li–air battery, in its non-aqueous implementation holds the promise of providing a specific energy considerably higher than conventional LIBs ( $\sim 2000$  vs.  $\sim 600 \text{ Wh kg}^{-1}$ ).<sup>5</sup> The non-aqueous Li–O<sub>2</sub> battery is, in its most simple design, comprised of a Li-metal anode, an electrolyte, and a porous cathode wherein oxygen gas is reduced and reacts with  $\text{Li}^+$  cations (Fig. 4).<sup>4–7</sup> The oxygen reduction reaction (ORR) and plausible subsequent reactions are described below. Lithium peroxide ( $\text{Li}_2\text{O}_2$ ) is the dominant discharge product.<sup>139,140</sup>






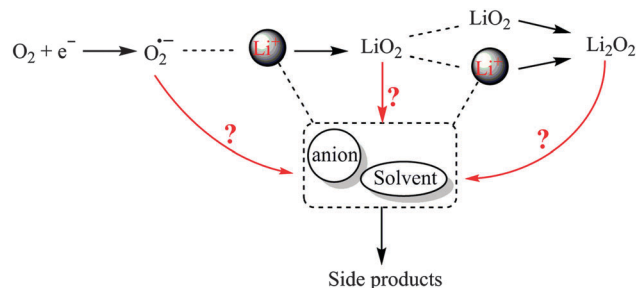


Fig. 5 A schematic illustration of possible parasitic reactions of  $\text{O}_2^-$  and  $\text{LiO}_2$  with  $\text{Li}^+$ , solvents, and anions resulting in  $\text{Li}_2\text{O}_2$  and/or side products in Li–O<sub>2</sub> cells.



The thermodynamic potential of the reactions is within the ESW of most aprotic electrolytes, and thus, the ORR products are predicted to only be Li–O compounds. Therefore, the passivation to mainly worry about is the Li-metal anode and reactions with water/ $\text{CO}_2$  from the air. Nevertheless, it is now well accepted that the discharge products contain different compounds formed from the degradation of the electrolyte in contact with intermediate and final reaction products.<sup>141–146</sup> Superoxide radical anion ( $\text{O}_2^-$ ) and lithium superoxide ( $\text{LiO}_2$ ) formed during ORR can attack solvents or Li-salts, instead of reacting with  $\text{Li}^+$  cations to form the final reaction products (see, Fig. 5). The charge reaction or oxygen evolution reaction (OER) is accompanied with overpotentials originating from poor conductivity of  $\text{Li}_2\text{O}_2$  or side products such as  $\text{Li}_2\text{CO}_3$ .<sup>147–151</sup> As a result, the anodic (oxidative) stability of electrolyte solvents and salts may become a challenge for electrolytes with limited ESW.

Beyond the different reaction processes, the choice of Li-salts impacts the viscosity, the oxygen solubility, and the wettability of the electrolytes.<sup>72,152–154</sup> Fig. 6 shows discharge curves in cells with different Li-salts dissolved in a DME:DOL

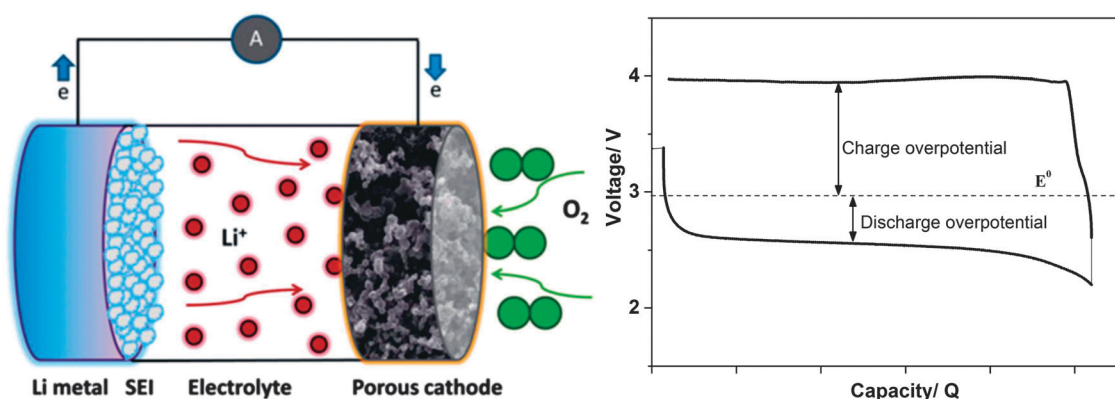


Fig. 4 A schematic drawing of a Li–O<sub>2</sub> cell (left) and typical galvanostatic discharge–charge curves showing overpotentials (right).



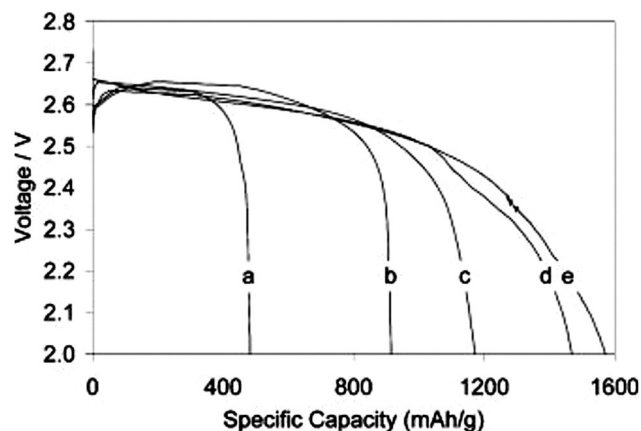


Fig. 6 Discharge curves of Li-O<sub>2</sub> cells using 1 M of: (a) LiBETI, (b) LiTFSI, (c) LiTf, and (d, e) LiBr dissolved in DME:DOL (1:1).<sup>72</sup>

solvent mixture, displaying that the discharge capacity increases as: LiBr > LiTriflate > LiTFSI > LiBETI. This was attributed to both the viscosity and the oxygen solubility of the electrolytes being altered by the Li-salts.<sup>72</sup> Equally important, a Li-salt should promote the formation of a proper SEI on the Li-metal anode (see Section 4).<sup>155</sup>

Early studies on the Li-O<sub>2</sub> battery utilized the most common LIBs salt *i.e.* the LiPF<sub>6</sub>. Subsequent investigations revealed that LiPF<sub>6</sub> salt is unstable in Li-O<sub>2</sub> batteries<sup>156–163</sup> and in particular X-ray photoelectron spectroscopy (XPS) studies have revealed that it decomposes to LiF, Li<sub>x</sub>PF<sub>y</sub>O<sub>z</sub>, and other P-O containing compounds during cell cycling.<sup>156–159</sup> FT-IR, NMR, X-ray diffraction (XRD), and non-resonant inelastic X-ray scattering (NIXS) results indicate similar findings.<sup>158–160</sup> LiF and other degradation products of LiPF<sub>6</sub> can remain on the surface of cathode, and

consequently, passivate the surfaces and/or block the pores. These results highlight the challenges of designing an electrolyte for Li-O<sub>2</sub> cells despite all these decomposition reactions occurring at potentials ( $\sim 2.5$ – $2.7$  V vs. Li<sup>+</sup>/Li<sup>0</sup>) well within the electrochemical stability window of the electrolyte.

The degradation of the LiPF<sub>6</sub> salt can be attributed to parasitic reactions with (i) intermediate and/or (ii) final ORR products. The former include degradation by O<sub>2</sub><sup>•−</sup> and LiO<sub>2</sub>, while the latter refers to degradation of the LiPF<sub>6</sub> salt by Li<sub>2</sub>O<sub>2</sub>.<sup>140,161,162,164</sup> Another common source of parasitic reactions is trace water, which has shown to substantially alter performance of the Li-O<sub>2</sub> cells.<sup>75,96</sup> The presence of water contamination commonly leads to an increase in the first discharge capacity, but also the formation of LiOH.<sup>96,157</sup> In the presence of water, LiPF<sub>6</sub> readily forms HF, which consequently degrade cell components.

The degradation of LiPF<sub>6</sub> guided researchers to study other Li-salts, often previously used in LIBs. LiTFSI has been widely used in Li-O<sub>2</sub> cells, but the TFSI anion has been shown to be unstable vs. ORR and OER in ether- and sulfone-based electrolyte solvents.<sup>157,159,164–166</sup> LiTf has been used in several studies indicating high re-chargeability, however, the salt stability is still under debate.<sup>159,167</sup> A unique feature of LiTf is the very high DN of the Tf anion (DN = 16.9) compared to all other anions employed (see Table 2). This could be favorable for Li-O<sub>2</sub> cells since it has been shown that a high DN of electrolytes results in increase higher solubility of LiO<sub>2</sub> as well as the discharge capacity of Li-O<sub>2</sub> cells.<sup>74–76</sup> Degradation of LiTFSI and LiTf both result in the formation of LiF and -CF<sub>3</sub>.<sup>157,159,164–166</sup> Similarly, LiF has been detected as a degradation product of the LiBF<sub>4</sub> salt.<sup>157,159,161</sup>

Taking into account that LiF always forms when any of the aforementioned Li-salts are used, a fluorine-free anion could arguably improve the performance. Hence, LiBison was used,<sup>168</sup>

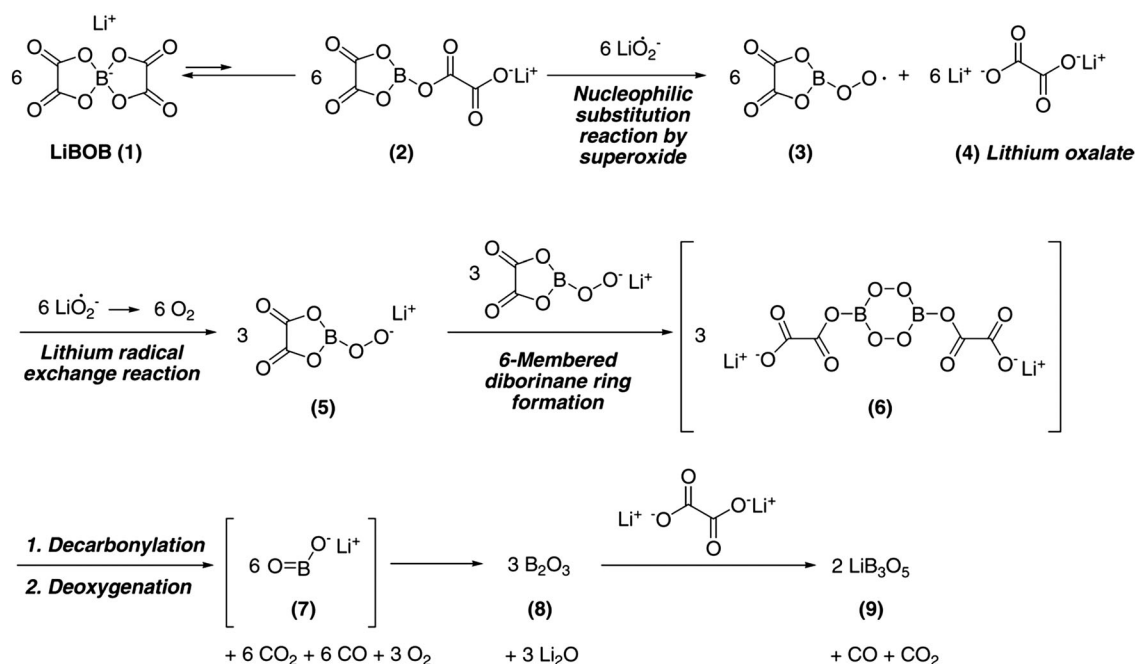


Fig. 7 Proposed mechanism for decomposition of LiBOB by superoxide radicals, obtained from Hyung Oh *et al.*<sup>170</sup>

but here the B–C bonds were found to break and form  $\text{B}_2\text{O}_3$  during cycling. For LiBison, the solvent chemistry also influences the degradation.<sup>168</sup> Another non-fluorinated Li-salt is LiBOB, which has also been shown to decompose.<sup>159,169–172</sup> Nazar *et al.* proposed a decomposition mechanism by superoxide radicals resulting in formation of lithium oxalate and lithium triborate (Fig. 7).<sup>170</sup> Although it has, and will have, no industrial application, due to severe safety issues,  $\text{LiClO}_4$  has been used in several academic studies reporting high re-chargeability of Li– $\text{O}_2$  cells.<sup>173,174</sup> The relatively higher stability of  $\text{LiClO}_4$  suggests it to continue to be suitable for the purpose of tests and development at the research level.<sup>157,159,169</sup>

Alongside the “super- concentrated” electrolyte approach for Li-metal and Li–S batteries, two studies have recently showed that a relatively high concentration of Li-salt, 3–5 M, can also improve the performance of Li– $\text{O}_2$  batteries.<sup>175,176</sup> These studies suggested the mechanism of protection to be that the superoxide radical now has a higher probability to react with solvated  $\text{Li}^+$  than with solvent molecules.

Alongside practical cell studies, the stability of various Li-salts has also been addressed by quantum chemical computational methods. Due to the vast computational cost associated with analyzing reactions within the Li– $\text{O}_2$  system properly as high level accuracy methods are needed to describe, *e.g.* interactions of the salt with the redoxactive molecule or solvent and the solvation structure of salt in solution,<sup>177</sup> only a limited set of studies have been performed thus far. Du *et al.* combined *ab initio* molecular dynamics (AIMD) and density functional theory (DFT) calculations at the B3LYP level to investigate the hydrolytic stability of LiTFSI, LiTf, and  $\text{LiPF}_6$  in tri(ethylene glycol)-substituted trimethylsilane (1NM3) and tetraglyme, respectively.<sup>158</sup>  $\text{LiPF}_6$  was shown to react with even small amounts of  $\text{H}_2\text{O}$  in 1NM3, whereas LiTf showed a much higher stability. All three salts were, however, found to be compatible with TEGDME. It should be noted that the investigated system sizes are small and the time-scales short, so additional verification is needed. Subsequent work by the Lau *et al.* found that LiBOB leads to the formation lithium oxalate during discharge and, according to DFT calculations, the formation of lithium oxalate is exothermic and thermodynamically favorable while LiBOB probably is not a suitable salt for the Li– $\text{O}_2$  battery.<sup>171</sup>

## 6. Li-salts for Li–S batteries

The Li–S battery concept has the promise of both very high energy densities ( $2567 \text{ W h kg}^{-1}$  and  $2800 \text{ W h l}^{-1}$ ) and the use of, in principle, an extremely in-expensive cathode material – sulfur.<sup>9</sup> The overwhelming part of the total number of Li–S battery studies has, in similarity to Li– $\text{O}_2$  batteries, been performed during the last decade and thus most Li-salts cited above have been available. Just as for Li– $\text{O}_2$  batteries, there is currently no Li-salt which has been specially designed for Li–S batteries, why the most commonly chosen Li-salts differs. In order to understand the specific choices made, the special Li–S battery demands on the electrolyte (and the Li-salt) must first be properly understood.

The overall possible chemistry choices for Li–S non-aqueous organic liquid electrolytes (solvents, salts, additives) as well as other types of electrolytes (ionic liquid based and non-liquid concepts) have recently been reviewed.<sup>77</sup> The Li–S battery has one strong common feature with the Li– $\text{O}_2$  battery – the use of a Li-metal anode, which indeed is meta-stable *vs.* the prevailing electrolytes used and is why additives like  $\text{LiNO}_3$  have been employed; although with rather unsatisfactory results.<sup>178</sup> The other special situation is the need for the electrolyte to be stable *vs.* the various poly-sulfides (PS) created during cell cycling. Another aspect of the same feature is whether the choice of Li-salt can affect the solubility of the PS in total and/or selectively (short-chain *vs.* long-chain PS). To date, many studies have focused on the solvent choice(s) with respect to affecting the PS solubility, but only a few reports on the influence of the choice of Li-salt.

Yet another notable difference is the rather limited ESW needed for the Li–S concept: max *ca.* 2.5 V (even including a proper safety margin) – which expands the choice of Li-salts much beyond the “usual suspects” from LIB studies *i.e.* LiTFSI is for Li–S cells a real contender to  $\text{LiPF}_6$ . Another candidate is LiTf – both these Li-salts are not viable for LIBs as Al (current collector) corrosion starts at *ca.* 2.8 V *vs.*  $\text{Li}^+/\text{Li}^\circ$ .<sup>179</sup> Indeed, during the last decade, these two salts, LiTFSI and LiTf, both at  $\sim 1 \text{ M}$  concentration,<sup>14</sup> totally dominate the Li–S literature. Their popularity is mainly based on their high thermal stabilities and compatibilities with the ether solvents often applied,<sup>180,181</sup> and, especially for LiTFSI, a high dissociation ability.<sup>182,183</sup> There is thus a renewed interest in LiTf, but despite its lower cost, it is not as popular as LiTFSI. This is because by employing LiTFSI the electrolyte conductivity approximately doubles compared to using LiTf; *e.g.* 1 M LiX in DME:PC (1:1) show conductivities of 11.2 and  $5.9 \text{ mS cm}^{-1}$  at  $20^\circ\text{C}$ , respectively.<sup>35,184</sup>

Along with the overall increase in Li–S research activities, electrolyte development has accelerated, based on variations of either the Li-salt concentration or other components being added to the electrolyte, as well as novel design concepts.<sup>69,185</sup> In addition, there are some Li-salts that we can foresee to be employed for Li–S batteries in the near future. As one example, the LiFSI salt could be employed just as well as the LiTFSI salt, and result in electrolytes of even higher conductivities (but with less stability), and we also propose that the LiTDI salt giving intermediate anodic stability could be employed – but there are yet some question marks concerning also this salt's stability *vs.* Li-metal anodes.<sup>59,61</sup> As a very novel salt alternative the  $\text{Li}[\text{B}(\text{OCH}_2\text{CF}_3)_4]$  borate salt was recently launched; stable up to 4.8 V *vs.*  $\text{Li}^+/\text{Li}^\circ$  and tested in a Li–S cell set-up,<sup>186</sup> whilst providing Coulombic efficiencies of 97% for each cycle for the 40 cycles shown. Notable is the use of a 0.2 M salt concentration in DME:DOL 1:1 wt% in this study, despite no clear motivation for this rather low concentration – as electrolytes based on this salt were easily made up to 0.8 M.

Having outlined the requirements needed for Li–S electrolytes and the Li-salt candidates most likely to fulfil these, there is a need for controlled studies in order to analyse the unique rôle of each choice of Li-salt for the Li–S performance or other specific behaviour. In most studies employing several different





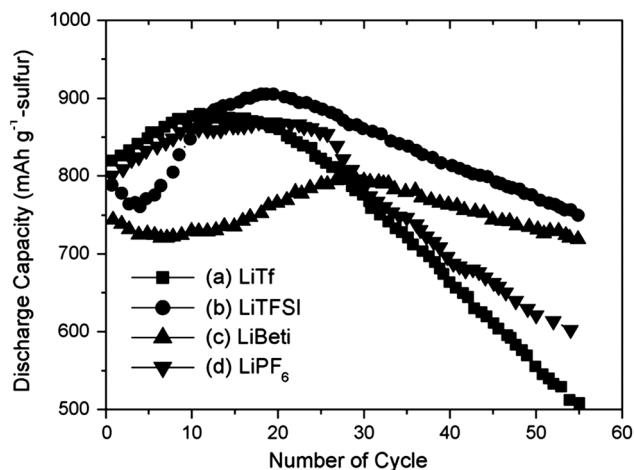


Fig. 8 Cycling performance of Li-S cells using DME/DOL (4:1, v:v) solvent mixture with a 1 M concentration of different salts: (a) LiTf; (b) LiTFSI; (c) LiBeti; (d) LiPF<sub>6</sub>. Modified from Kim *et al.*<sup>189</sup>

Li-salts concomitant changes in the solvent composition hinder any unambiguous analysis.<sup>187,188</sup> However, there is a rather limited number of studies where the Li-salt is the only variable and all other parameters constant. Kim *et al.*<sup>189</sup> studied four Li-salts in the same solvent; LiPF<sub>6</sub>, LiTFSI, LiTf, and LiBETI and Gao *et al.*<sup>190</sup> did the same for three salts: LiTf, LiPF<sub>6</sub>, and LiClO<sub>4</sub>. Both these studies used standard Li-S battery electrolyte solvents DME/DOL (4:1) and tetraglyme, respectively, and a salt concentration of 1 M.

In the work of Kim *et al.*,<sup>189</sup> the Li-salts were ranked by the initial capacity and capacity decay of the Li-S cell – the latter taken as the discharge capacity at the 50th cycle: LiTFSI (770 mA h g<sup>-1</sup>) > LiBETI (730 mA h g<sup>-1</sup>) > LiPF<sub>6</sub> (620 mA h g<sup>-1</sup>) > LiTf (560 mA h g<sup>-1</sup>) (Fig. 8). The film forming properties at the lithium anode surface, in the field of Li-S batteries an often neglected factor in comparison to the ability to handle PS solubility, was suggested as a partial explanation for the markedly better performance of the LiTFSI and LiBETI based electrolytes, as also observed earlier with PC as the solvent.<sup>120</sup>

In contrast, Gao *et al.*<sup>190</sup> claimed to find no significant effect on Li-S cell performance by altering the Li-salt, despite the data contained in the publication which clearly show that the cells with the LiClO<sub>4</sub> salt demonstrated a quite significant stabilization (for the limited 10 charge-discharge cycles made).

Another path forward in the research on Li-S battery electrolytes is what has been coined “quasi ionic liquids” or more precisely equimolar mixtures of a glyme solvent Gn (*e.g.* triglyme, G3) and a Li-salt to create [Li(Gn)]X species.<sup>191</sup> This is a quite intriguing concept, with the salt concentration totally dependent on how to obtain the 1:1 Li:Gn ratio. It has been applied for LiBETI, LiTFSI, LiTf, LiNO<sub>3</sub>, and LiBF<sub>4</sub>, and dramatic differences in cell performance have been reported.<sup>191</sup> The PS solubility was much higher in [Li(G3)]NO<sub>3</sub> and [Li(G3)]Tf as compared to the remaining electrolytes, resulting in a poor Li-S cell performance. Poor cell performance was also found for [Li(G3)]BF<sub>4</sub>, and BF<sub>4</sub><sup>-</sup> was also suggested to decompose in the

presence of PS. Ueno *et al.*<sup>191</sup> also made one of very few attempts to at the molecular level explain the poor performance observed at a macroscopic level; a stronger interaction of the Tf and NO<sub>3</sub><sup>-</sup> anions with Li<sup>+</sup> was suggested and as a consequence slightly less stable [Li(G3)]<sup>+</sup> complexes resulting. Thus, also for the quasi ionic liquid based electrolytes, LiTFSI and LiBETI are the two best Li-salts tested.

Another line of work is that of studying the rôle of the salt concentration. Using both LiClO<sub>4</sub> and LiTf, Kolosnitsyn *et al.*<sup>192</sup> studied how the salt concentration affects the viscosity, the conductivity, and the PS solubility of TMS based electrolytes. They also found the viscosity to increase with salt basicity, LiClO<sub>4</sub> > LiTf, and at higher LiClO<sub>4</sub> concentrations, the viscosity rapidly increased – likely due to dynamic cross-linking of PS chains by the ‘free’ Li<sup>+</sup> ions present. While most studies, as mentioned previously, use a 1 M standard – the Li<sub>2</sub>S<sub>6</sub> PS solubility was found to have a minimum at ~0.3 M, while the conductivity had a maximum at 0.5 M. Two single salt studies of salt concentration are Chang *et al.*,<sup>193</sup> using LiTf to study the PS solubility, and Barchasz *et al.*<sup>194,195</sup> using LiTFSI between 0.1–2 M, the latter concluding that, in order to balance cost and performance, 1 M is still to be the recommended salt concentration. Very recently also the solubility of elemental sulfur (S) was quantitatively determined – using electrolytes with LiTFSI, LiClO<sub>4</sub>, LiBF<sub>4</sub>, and LiTf dissolved in both organic solvents and ionic liquids – combined creating no less than 22 electrolytes.<sup>196</sup> The choice of Li-salt was by chromatography found to be of much less importance than the choice of solvent and the salt concentration (either 0.1 or 1 M) – for the former the solubility varied by maximum *ca.* 25% (at 1 M) while the choice of solvent could indeed alter the S solubility by orders of magnitude.

Even higher salt concentrations have recently attracted a lot of interest. Shin *et al.*<sup>197</sup> studied LiTFSI based electrolytes up to 5 M concentration – obtaining less dissolution of PS at higher concentrations and also a decreased overcharge and an improved Coulombic efficiency. Moving to even higher LiTFSI concentrations in the “solvent-in-salt” (≤7 M) electrolytes by Suo *et al.*,<sup>69</sup> where the salt becomes the dominant component,

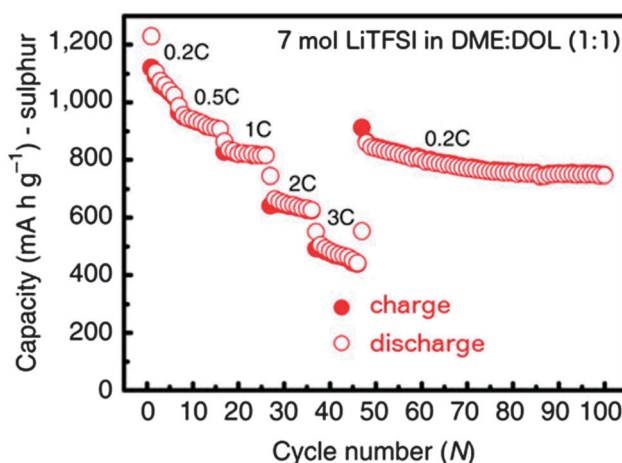


Fig. 9 Rate capability of a Li-S battery with 7 M LiTFSI in DME/DOL (1:1). Modified from Suo *et al.*<sup>69</sup>



PS dissolution was negligible and uniform Li-metal anode plating and stripping was demonstrated at a salt concentration of 7 M – close to the saturation limit. This resulted in high initial capacity, excellent rate capability ( $\leq 3$  C) (Fig. 9) – a property usually quite limiting for Li-S cells (in general cycling at  $C/20$  is commonly needed to get sustainable performance), a high capacity retention, and a high Coulombic efficiency – close to 100% for 100 cycles. The much higher viscosity compared to having a 1 M system resulted in only a slightly increased polarization.

While the concept of very high salt concentrations seems promising from a performance point of view – the main concern is cost; a large amount of a costly Li-salt may prove detrimental to the otherwise formally inexpensive Li-S battery design.<sup>198</sup> In this respect, the balance of performance and cost is delicate, but if a truly excellently working cell can be demonstrated, we do not believe that the cost carried by the Li-salt will be an obstacle to commercialization.

Overall, due to the rather different demands in terms of PS solubility and the limited ESW needed, the main problems of Li-S batteries as of today do not in any way originate in the Li-salt employed. On the contrary, the right salt (currently LiTFSI seems to be the main candidate) at the right concentration (rather much higher than 1 M it seems – in the light of both the quasi ionic liquid systems and the studies of Shin *et al.* and Suo *et al.*) can indeed enhance the performance of the cells.

## 7. Conclusions

The development of advanced batteries such as Li-metal, Li-O<sub>2</sub>, and Li-S batteries requires new electrolyte chemistries, which could (i) remain preserved during cell cycling and in contact with intermediate and final reaction products, and (ii) provide high Coulombic efficiency with a Li-metal anode. Though several Li-salts have been studied, none has provided a package of appropriated properties that LiPF<sub>6</sub> provides for LIBs with graphite anode and moderate voltage cathodes (3–4 V).

To date, virtually all of the studies focused on forming a stable SEI layer in carbonate solvent on Li-metal have failed to produce a robust electrode, which cycles with sufficient Coulombic efficiency and without dendrite formation. The examples highlighted in Section 4 provide evidence that significant advances can be realized with the right electrolyte chemistry, although the performance of Li anodes does not match traditional graphite materials. There are promising results coming out for IL-based and solid-state electrolytes, but these materials are still many years away from production. For those continuing to work on liquid electrolytes and the formation of passivation layers in contact with Li-metal, we recommend focusing on anions capable of forming polymerized and flexible structures, while optimizing the ionic transport. Indeed as noted by Xu, “an electrolyte with higher bulk ionic conductivity usually results in an SEI of lower impedance”.<sup>14</sup>

The Li-O<sub>2</sub> battery mainly suffers from degradation of electrolytes. Along with different solvents, several Li-salts including

LiPF<sub>6</sub>, LiTFSI, LiBF<sub>4</sub>, LiTf, LiBOB, Li[B(CN)<sub>4</sub>], and LiClO<sub>4</sub> have been employed, but they all degrade in cells. Therefore, a key step in the development of metal-oxygen batteries is to design Li-salts and electrolyte solvents which are electrochemically and chemically stable in presence of oxygen species such as superoxides and peroxides, when ORR and OER occur at the cathode. Such an electrolyte should also provide sufficient ionic conductivity, oxygen solubility, and anodic stability at high surface area cathodes. As a high DN of electrolyte solvents has been shown to increase the solubility of LiO<sub>2</sub> as well as the discharge capacity of Li-O<sub>2</sub> cells, LiTf could be a preferred Li-salt to be used together with high DN solvents. However, stability of LiTf in contact with all reactive species in long term cycling as well as its compatibility with Li-metal anode need to be more comprehensively explored. The complexity of oxygen batteries declines feasibility of achieving commercial Li-O<sub>2</sub> batteries in near future, but we believe that further research on metal-oxygen batteries will assist the battery community to develop new chemistries for electrochemical energy storage and conversion systems.

As for the employment of salts for Li-S cells, the LiTFSI and LiTf salts are commonly used and can assist in controlling the PS solubility, but only given a suitable solvent. Contrary to many other Li based battery concepts, the Li-S battery is not particularly limited by the choice of Li-salt (apart from the common issue of passivating layers for the Li-metal electrode). Exciting developments are those using very high salt concentrations and employing glymes in equimolar concentrations to the salt – both resulting in better cell cyclabilities.

## Acknowledgements

The authors acknowledge support of this work from the ReLIable project (project nr. 11-116792/0603-00462B) funded by the Danish Council for Strategic Research Programme Commission on Sustainable Energy and Environment under the Danish Innovation Foundation. A portion of this work (GMV) was supported by U.S. Department of Energy's Office of Basic Energy Science (DOE-BES), Division of Materials Sciences and Engineering, under contract with UT-Battelle, LLC. In addition, the UU/KTH StandUp for Energy as well as several of Chalmers Areas of Advance: Materials Science, Energy and Transport, the Swedish Foundation for Strategic Research (SSF) within the project Road to load and the Battery Fond administrated by the Swedish Energy Agency, are all acknowledged for support.

## References

- 1 B. Dunn, H. Kamath and J.-M. Tarascon, *Science*, 2011, **334**, 928–935.
- 2 F. T. Wagner, B. Lakshmanan and M. F. Mathias, *J. Phys. Chem. Lett.*, 2010, **1**, 2204–2219.
- 3 W. Xu, J. Wang, F. Ding, X. Chen, E. Nasybulin, Y. Zhang and J.-G. Zhang, *Energy Environ. Sci.*, 2014, **7**, 513–537.



- 4 J. Christensen, P. Albertus, R. S. Sanchez-Carrera, T. Lohmann, B. Kozinsky, R. Liedtke, J. Ahmed and A. Kojic, *J. Electrochem. Soc.*, 2012, **159**, R1–R30.
- 5 Y.-C. Lu, B. M. Gallant, D. G. Kwabi, J. R. Harding, R. R. Mitchell, M. S. Whittingham and Y. Shao-Horn, *Energy Environ. Sci.*, 2013, **6**, 750–768.
- 6 A. C. Luntz and B. D. McCloskey, *Chem. Rev.*, 2014, **114**, 11721–11750.
- 7 P. G. Bruce, S. A. Freunberger, L. J. Hardwick and J.-M. Tarascon, *Nat. Mater.*, 2012, **11**, 19–29.
- 8 A. Manthiram, Y. Fu and Y.-S. Su, *Acc. Chem. Res.*, 2012, **46**, 1125–1134.
- 9 X. Ji and L. F. Nazar, *J. Mater. Chem.*, 2010, **20**, 9821–9826.
- 10 K. Xu, *Chem. Rev.*, 2014, **114**, 11503–11618.
- 11 D. Aurbach, *Nonaqueous Electrochemistry*, Marcel Dek., New York, 1999.
- 12 G.-A. Nazri and G. Pistoia, *Lithium Batteries: Science and Technology*, Springer, 2003.
- 13 R. A. Huggins, *Advanced Batteries*, Springer US, Boston, MA, 2009.
- 14 K. Xu, *Chem. Rev.*, 2004, **104**, 4303–4418.
- 15 W. A. Henderson, *Electrolytes for Lithium and Lithium-Ion Batteries*, Springer New York, NY, 2014, vol. 58.
- 16 H. J. Gores, J. Barthel, S. Zugmann and D. Moosbauer, *Handbook of Battery Materials*, Wiley-VCH Verlag GmbH & Co. KGaA, Weinheim, Germany, 2011.
- 17 W. Tang, L. Liu, Y. Zhu, H. Sun, Y. Wu and K. Zhu, *Energy Environ. Sci.*, 2012, **5**, 6909–6913.
- 18 X. Wang, Q. Qu, Y. Hou, F. Wang and Y. Wu, *Chem. Commun.*, 2013, **49**, 6179–6181.
- 19 Z. Chang, X. Wang, Y. Yang, J. Gao, M. Li, L. Liu and Y. Wu, *J. Mater. Chem. A*, 2014, **2**, 19444–19450.
- 20 S. J. Visco, V. Y. Nimon, A. Petrov, K. Pridatko, N. Goncharenko, E. Nimon, L. De Jonghe, Y. M. Volkovich and D. a. Bograchev, *J. Solid State Electrochem.*, 2014, **18**, 1443–1456.
- 21 V. Aravindan, J. Gnanaraj, S. Madhavi and H.-K. Liu, *Chem. – Eur. J.*, 2011, **17**, 14326–14346.
- 22 R. W. Schmitz, P. Murmann, R. Schmitz, R. Müller, L. Krämer, J. Kasnatscheew, P. Isken, P. Niehoff, S. Nowak, G.-V. Röschenthaler, N. Ignatiev, P. Sartori, S. Passerini, M. Kunze, A. Lex-Balducci, C. Schreiner, I. Cekic-Laskovic and M. Winter, *Prog. Solid State Chem.*, 2014, **42**, 65–84.
- 23 T. Böttcher, B. Duda, N. Kalinovich, O. Kazakova, M. Ponomarenko, K. Vlasov, M. Winter and G.-V. Röschenthaler, *Prog. Solid State Chem.*, 2014, **42**, 202–217.
- 24 M. Marcinek, J. Syzdek, M. Marczewski, M. Piszcz, L. Niedzicki, M. Kalita, A. Plewa-Marczewska, A. Bitner, P. Wiczorek, T. Trzeciak, M. Kasprzyk, P. Łzak, Z. Zukowska, A. Zalewska and W. Wiczorek, *Solid State Ionics*, 2015, **276**, 107–126.
- 25 G. Pistoia, *J. Electrochem. Soc.*, 1971, **118**, 153–158.
- 26 C. D. Desjardins, T. G. Cadger, R. S. Salter, G. Donaldson and E. J. Caser, *J. Electrochem. Soc.*, 1985, **132**, 529–533.
- 27 J. O. Besenhard and G. Eichinger, *J. Electroanal. Chem. Interfacial Electrochem.*, 1976, **68**, 1–18.
- 28 V. R. Koch, *J. Power Sources*, 1981, **6**, 357–370.
- 29 A. M. Andersson, M. Herstedt, A. G. Bishop and K. Edström, *Electrochim. Acta*, 2002, **47**, 1885–1898.
- 30 R. Fong, U. von Sacken and J. R. Dahn, *J. Electrochem. Soc.*, 1990, **137**, 2009–2013.
- 31 Y. Ein-Eli, B. Markovsky, D. Aurbach, Y. Carmeli, H. Yamin and S. Luski, *Electrochim. Acta*, 1994, **39**, 2559–2569.
- 32 A. M. Andersson, K. Edström and J. O. Thomas, *J. Power Sources*, 1999, **81–82**, 8–12.
- 33 Z. Ogumi and M. Inaba, *Bull. Chem. Soc. Jpn.*, 1998, **71**, 521–534.
- 34 E. Peled, D. Golodnitsky, C. Menachem and D. Bar-Tow, *J. Electrochem. Soc.*, 1998, **145**, 3482–3486.
- 35 J. T. Dudley, D. P. Wilkinson, G. Thomas, R. LeVae, S. Woo, H. Blom, C. Horvath, M. W. Juzkow, B. Denis, P. Juric, P. Aghakian and J. R. Dahn, *J. Power Sources*, 1991, **35**, 59–82.
- 36 M. Schmidt, U. Heider, A. Kuehner, R. Oesten, M. Jungnitz, N. Ignat'ev and P. Sartori, *J. Power Sources*, 2001, **97–98**, 557–560.
- 37 S. E. Sloop, J. K. Pugh, S. Wang, J. B. Kerr and K. Kinoshita, *Electrochem. Solid-State Lett.*, 2001, **4**, A42–A44.
- 38 A. M. Andersson and K. Edström, *J. Electrochem. Soc.*, 2001, **148**, A1100–A1109.
- 39 S. S. Zhang, K. Xu and T. R. Jow, *J. Electrochem. Soc.*, 2002, **149**, A586–A590.
- 40 N. Takami, T. Ohsaki, H. Hasebe and M. Yamamoto, *J. Electrochem. Soc.*, 2002, **149**, A9–A12.
- 41 S. Zhang, K. Xu and T. Jow, *J. Solid State Electrochem.*, 2003, **7**, 147–151.
- 42 W. Gorecki, M. Jeannin, E. Belorizky, C. Roux and M. Armand, *J. Phys.: Condens. Matter*, 1995, **7**, 6823–6832.
- 43 K. Xu, S. Zhang, T. R. Jow, W. Xu and C. A. Angell, *Electrochem. Solid-State Lett.*, 2002, **5**, A26–A29.
- 44 B. Fahys and M. Herlem, *J. Power Sources*, 1991, **34**, 183–188.
- 45 J. Foropoulos and D. D. DesMarteau, *Inorg. Chem.*, 1984, **23**, 3720–3723.
- 46 J. S. Gnanaraj, M. D. Levi, Y. Gofer, D. Aurbach and M. Schmidt, *J. Electrochem. Soc.*, 2003, **150**, A445–A454.
- 47 D. Di Censo, I. Exnar and M. Graetzel, *Electrochem. Commun.*, 2005, **7**, 1000–1006.
- 48 P. Murmann, P. Niehoff, R. Schmitz, S. Nowak, H. Gores, N. Ignatiev, P. Sartori, M. Winter and R. Schmitz, *Electrochim. Acta*, 2013, **114**, 658–666.
- 49 M. Ue, T. Fujii, Z.-B. Zhou, M. Takeda and S. Kinoshita, *Solid State Ionics*, 2006, **177**, 323–331.
- 50 S. Tsujioka, H. Takase, M. Takahashi and Y. Isono, *US Pat.*, 6849752 B2, 2005.
- 51 T. Küppers, E. Bernhardt, H. Willner, H. W. Rohm and M. Köckerling, *Inorg. Chem.*, 2005, **44**, 1015–1022.
- 52 J. Scheers, P. Johansson and P. Jacobsson, *J. Electrochem. Soc.*, 2008, **155**, A628–A634.
- 53 J. Scheers, J. Pitawala, F. Thebault, J.-K. Kim, J.-H. Ahn, A. Matic, P. Johansson and P. Jacobsson, *Phys. Chem. Chem. Phys.*, 2011, **13**, 14953–14959.
- 54 J. Scheers, D.-H. Lim, J.-K. Kim, E. Paillard, W. A. Henderson, P. Johansson, J.-H. Ahn and P. Jacobsson, *J. Power Sources*, 2014, **251**, 451–458.



- 55 M. Egashira, B. Scrosati, M. Armand, S. Béranger and C. Michot, *Electrochem. Solid-State Lett.*, 2003, **6**, A71–A73.
- 56 C. Herriot, S. Khatun, E. T. Fox, P. Judeinstein, M. Armand, W. A. Henderson and S. Greenbaum, *J. Phys. Chem. Lett.*, 2012, **3**, 441–444.
- 57 C. Liao, K. S. Han, L. Baggetto, D. A. Hillesheim, R. Custelcean, E.-S. Lee, B. Guo, Z. Bi, D. Jiang, G. M. Veith, E. W. Hagaman, G. M. Brown, C. Bridges, M. P. Paranthaman, A. Manthiram, S. Dai and X.-G. Sun, *Adv. Energy Mater.*, 2014, **4**, 1301368.
- 58 L. Niedzicki, S. Grugeon, S. Laruelle, P. Judeinstein, M. Bukowska, J. Prejzner, P. Szczeciński, W. Wieczorek and M. Armand, *J. Power Sources*, 2011, **196**, 8696–8700.
- 59 J. Scheers, P. Johansson, P. Szczeciński, W. Wieczorek, M. Armand and P. Jacobsson, *J. Power Sources*, 2010, **195**, 6081–6087.
- 60 I. Krossing and I. Raabe, *Angew. Chem., Int. Ed.*, 2004, **43**, 2066–2090.
- 61 P. Johansson, H. Nilsson, P. Jacobsson and M. Armand, *Phys. Chem. Chem. Phys.*, 2004, **6**, 895–899.
- 62 P. Johansson, *Phys. Chem. Chem. Phys.*, 2007, **9**, 1493–1498.
- 63 M. Armand and P. Johansson, *J. Power Sources*, 2008, **178**, 821–825.
- 64 E. Jónsson and P. Johansson, *Phys. Chem. Chem. Phys.*, 2012, **14**, 10774–10779.
- 65 M. Carboni, R. Spezia and S. Brutti, *J. Phys. Chem. C*, 2014, **118**, 24221–24230.
- 66 J. Scheers, E. Jónsson, P. Jacobsson and P. Johansson, *Electrochemistry*, 2012, **80**, 18–25.
- 67 H. P. Chen, J. W. Fergus and B. Z. Jang, *J. Electrochem. Soc.*, 2000, **147**, 399–406.
- 68 S.-K. Jeong, H.-Y. Seo, D.-H. Kim, H.-K. Han, J.-G. Kim, Y. B. Lee, Y. Iriyama, T. Abe and Z. Ogumi, *Electrochem. Commun.*, 2008, **10**, 635–638.
- 69 L. Suo, Y.-S. Hu, H. Li, M. Armand and L. Chen, *Nat. Commun.*, 2013, **4**, 1481.
- 70 H.-S. Kim and C.-S. Jeong, *Bull. Korean Chem. Soc.*, 2011, **32**, 3682–3686.
- 71 W. Xu and C. A. Angell, *Electrochem. Solid-State Lett.*, 2001, **4**, L3.
- 72 J. Read, *J. Electrochem. Soc.*, 2006, **153**, A96–A100.
- 73 V. Gutmann, *Coord. Chem. Rev.*, 1976, **18**, 225–255.
- 74 L. Johnson, C. Li, Z. Liu, Y. Chen, S. A. Freunberger, J.-M. Tarascon, P. C. Ashok, B. B. Praveen, K. Dholakia and P. G. Bruce, *Nat. Chem.*, 2014, **6**, 1–9.
- 75 N. B. Aetukuri, B. D. McCloskey, J. M. García, L. E. Krupp, V. Viswanathan and A. C. Luntz, *Nat. Chem.*, 2015, **7**, 50–56.
- 76 K. M. Abraham, *J. Electrochem. Soc.*, 2015, **162**, A3021–A3031.
- 77 J. Scheers, S. Fantini and P. Johansson, *J. Power Sources*, 2014, **255**, 204–218.
- 78 W. Linert, A. Camard, M. Armand and C. Michot, *Coord. Chem. Rev.*, 2002, **226**, 137–141.
- 79 P. Johansson, *J. Phys. Chem. A*, 2006, **110**, 12077–12080.
- 80 E. Jónsson and P. Johansson, *Phys. Chem. Chem. Phys.*, 2015, **17**, 3697–3703.
- 81 K. Edström, T. Gustafsson and J. O. Thomas, *Electrochim. Acta*, 2004, **50**, 397–403.
- 82 S.-T. Myung, Y. Hitoshi and Y.-K. Sun, *J. Mater. Chem.*, 2011, **21**, 9891–9911.
- 83 A. Hofmann, M. Schulz, V. Winkler and T. Hanemann, *J. Electrochem. Soc.*, 2014, **161**, A431–A438.
- 84 S. Wilken, M. Treskow, J. Scheers, P. Johansson and P. Jacobsson, *RSC Adv.*, 2013, **3**, 16359–16364.
- 85 B. G. Nolan and S. H. Strauss, *J. Electrochem. Soc.*, 2003, **150**, A1726–A1734.
- 86 J. Jiang, H. Fortier, J. N. Reimers and J. R. Dahn, *J. Electrochem. Soc.*, 2004, **151**, A609–A613.
- 87 U. von Sacken, E. Nodwell, A. Sundler and J. R. Dahn, *Solid State Ionics*, 1994, **69**, 284–290.
- 88 K. Sato, *Solid State Ionics*, 2002, **148**, 463–466.
- 89 G. V. Zhuang, H. Yang, P. N. Ross, K. Xu and T. R. Jow, *Electrochem. Solid-State Lett.*, 2006, **9**, A64–A68.
- 90 L. Yang, C. Smith, C. Patrissi, C. R. Schumacher and B. L. Lucht, *J. Power Sources*, 2008, **185**, 1359–1366.
- 91 Sigma-Aldrich, <http://www.sigmaaldrich.com/materialsscience/material-science-products.html?TablePage=19295337>.
- 92 L. Yang, H. Zhang, P. F. Driscoll, B. Lucht and J. B. Kerr, *ECS Trans.*, 2011, **33**, 57–69.
- 93 H.-B. Han, S.-S. Zhou, D.-J. Zhang, S.-W. Feng, L.-F. Li, K. Liu, W.-F. Feng, J. Nie, H. Li, X.-J. Huang, M. Armand and Z.-B. Zhou, *J. Power Sources*, 2011, **196**, 3623–3632.
- 94 Y. Hu, H. Li, X. Huang and L. Chen, *Electrochem. Commun.*, 2004, **6**, 28–32.
- 95 K. Tasaki, K. Kanda, S. Nakamura and M. Ue, *J. Electrochem. Soc.*, 2003, **150**, A1628–A1636.
- 96 S. Meini, M. Piana, N. Tsiouvaras, A. Garsuch and H. A. Gasteiger, *Electrochem. Solid-State Lett.*, 2012, **15**, A45–A48.
- 97 M. J. Trahan, PhD thesis, Northeastern University, US, 2014.
- 98 R. D. W. Kemmitt, D. R. Russell and D. W. A. Sharp, *J. Chem. Soc.*, 1963, 4408.
- 99 W. N. Smith, *US Pat.*, 3607020, 1970.
- 100 R. A. Wiesboeck, *US Pat.*, 3654330, 1972.
- 101 *Fluorinated Materials for Energy Conversion*, ed. T. Nakajima and H. Groult, Elsevier, 1st edn, 2005.
- 102 D. J. Salmon, W. Barnette and R. A. Baenett, *US Pat.*, 5378445, 1995.
- 103 H.-J. Belt, D. Seffer and W. Rudolph, *US Pat.*, 5866093, 1999.
- 104 P. Bonnet, S. Perdrieux and S. G. Schon, *US Pat.*, 5935541, 1999.
- 105 A. Subramaniam, T. Vasudevan and R. Gangadharan, *US Pat.*, 6824754 B2, 2004.
- 106 J.-H. Kim, H. Umeda, M. Ohe, S. Yonezawa and M. Takashima, *Chem. Lett.*, 2011, **40**, 360–361.
- 107 H. Kim, G. Jeong, Y.-U. Kim, J.-H. Kim, C.-M. Park and H.-J. Sohn, *Chem. Soc. Rev.*, 2013, **42**, 9011–9034.
- 108 D. Aurbach, *J. Power Sources*, 2000, **89**, 206–218.
- 109 A. Ferrese and J. Newman, *J. Electrochem. Soc.*, 2014, **161**, A1350–A1359.
- 110 C. Monroe and J. Newman, *J. Electrochem. Soc.*, 2005, **152**, A396–A404.
- 111 S. Kalnaus, A. S. Sabau, W. E. Tenhaeff, N. J. Dudney and C. Daniel, *J. Power Sources*, 2012, **201**, 280–287.





- 112 D. Blanchard, A. Nale, D. Sveinbjörnsson, T. M. Eggenhuisen, M. H. W. Verkuijen, Suwarno, T. Vegge, A. P. M. Kentgens and P. E. de Jongh, *Adv. Funct. Mater.*, 2015, **25**, 184–192.
- 113 J. B. Bates, N. J. Dudney, D. C. Lubben, G. R. Gruzalski, B. S. Kwak, X. Yu and R. A. Zuhr, *J. Power Sources*, 1995, **54**, 58–62.
- 114 N. J. Dudney, *J. Power Sources*, 2000, **89**, 176–179.
- 115 S. Neuhold, D. J. Schroeder and J. T. Vaughey, *J. Power Sources*, 2012, **206**, 295–300.
- 116 S. Shui Zhang, *Electrochem. Commun.*, 2006, **8**, 1423–1428.
- 117 R. Herr, *Electrochim. Acta*, 1990, **35**, 1257–1265.
- 118 D. Aurbach, *Solid State Ionics*, 2002, **148**, 405–416.
- 119 G. E. Blomgren, *J. Power Sources*, 1999, **81–82**, 112–118.
- 120 K. Naoi, M. Mori, Y. Naruoka, W. M. Lamanna and R. Atanasoski, *J. Electrochem. Soc.*, 1999, **146**, 462–469.
- 121 M. Odziemkowski and D. E. Irish, *J. Electrochem. Soc.*, 1992, **139**, 3063–3074.
- 122 M. Odziemkowski and D. E. Irish, *J. Electrochem. Soc.*, 1993, **140**, 1546–1555.
- 123 D. Rahner, *J. Power Sources*, 1999, **81–82**, 358–361.
- 124 K. Nishikawa, Y. Fukunaka, T. Sakka, Y. H. Ogata and J. R. Selman, *J. Electrochem. Soc.*, 2007, **154**, A943–A948.
- 125 D. Aurbach and M. Moshkovich, *J. Electrochem. Soc.*, 1998, **145**, 2629–2639.
- 126 K. Nishikawa, T. Mori, T. Nishida, Y. Fukunaka and M. Rosso, *J. Electroanal. Chem.*, 2011, **661**, 84–89.
- 127 X.-G. Sun, C. Liao, L. Baggetto, B. Guo, R. R. Unocic, G. M. Veith and S. Dai, *J. Mater. Chem. A*, 2014, **2**, 7606–7614.
- 128 T. Schedlbauer, B. Hoffmann, S. Krüger, H. Gores and M. Winter, *Energies*, 2013, **6**, 3481–3505.
- 129 T. Schedlbauer, S. Krüger, R. Schmitz, R. W. Schmitz, C. Schreiner, H. J. Gores, S. Passerini and M. Winter, *Electrochim. Acta*, 2013, **92**, 102–107.
- 130 T. Schedlbauer, U. C. Rodehorst, C. Schreiner, H. J. Gores and M. Winter, *Electrochim. Acta*, 2013, **107**, 26–32.
- 131 M. Wu, Z. Wen, Y. Liu, X. Wang and L. Huang, *J. Power Sources*, 2011, **196**, 8091–8097.
- 132 K. Chung, J.-D. Lee, E.-J. Kim, W.-S. Kim, J.-H. Cho and Y.-K. Choi, *Microchem. J.*, 2003, **75**, 71–77.
- 133 W. Walker, V. Giordani, J. Uddin, V. S. Bryantsev, G. V Chase and D. Addison, *J. Am. Chem. Soc.*, 2013, **135**, 2076–2079.
- 134 M. Roberts, R. Younesi, W. Richardson, J. Liu, T. Gustafsson, J. Zhu and K. Edström, *ECS Electrochem. Lett.*, 2014, **3**, A62–A65.
- 135 V. Giordani, W. Walker, V. S. Bryantsev, J. Uddin, G. V Chase and D. Addison, *J. Electrochem. Soc.*, 2013, **160**, A1544–A1550.
- 136 F. Ding, W. Xu, G. L. Graff, J. Zhang, M. L. Sushko, X. Chen, Y. Shao, M. H. Engelhard, Z. Nie, J. Xiao, X. Liu, P. V Sushko, J. Liu and J.-G. Zhang, *J. Am. Chem. Soc.*, 2013, **135**, 4450–4456.
- 137 J. Qian, W. a. Henderson, W. Xu, P. Bhattacharya, M. Engelhard, O. Borodin and J.-G. Zhang, *Nat. Commun.*, 2015, **6**, 6362.
- 138 Y. Yamada, K. Furukawa, K. Sodeyama, K. Kikuchi, M. Yaegashi, Y. Tateyama and A. Yamada, *J. Am. Chem. Soc.*, 2014, **136**, 5039–5046.
- 139 Y.-C. Lu, H. a. Gasteiger, M. C. Parent, V. Chiloyan and Y. Shao-Horn, *Electrochem. Solid-State Lett.*, 2010, **13**, A69–A72.
- 140 C. O. Laoire, S. Mukerjee, K. M. Abraham, E. J. Plichta and M. A. Hendrickson, *J. Phys. Chem. C*, 2009, **113**, 20127–20134.
- 141 C. M. Ó. Laoire, PhD thesis, Northeastern University, US, 2010.
- 142 R. Younesi, PhD thesis, Uppsala University, Sweden, 2012.
- 143 N. Garcia-Araez and P. Novák, *J. Solid State Electrochem.*, 2013, **17**, 1793–1807.
- 144 M. Balaish, A. Kraytsberg and Y. Ein-Eli, *Phys. Chem. Chem. Phys.*, 2014, **16**, 2801–2822.
- 145 R. Younesi, P. Norby and T. Vegge, *ECS Electrochem. Lett.*, 2014, **3**, A15–A18.
- 146 M. M. Storm, R. E. Johnsen, R. Younesi and P. Norby, *J. Mater. Chem. A*, 2015, **3**, 3113–3119.
- 147 Y. S. Mekonnen, K. B. Knudsen, J. S. G. Mýrdal, R. Younesi, J. Højberg, J. Hjelm, P. Norby and T. Vegge, *J. Chem. Phys.*, 2014, **140**, 121101.
- 148 J. Chen, J. S. Hummelshøj, K. S. Thygesen, J. S. G. Myrdal, J. K. Nørskov and T. Vegge, *Catal. Today*, 2011, **165**, 2–9.
- 149 J. M. Garcia-Lastra, J. S. G. Myrdal, R. Christensen, K. S. Thygesen and T. Vegge, *J. Phys. Chem. C*, 2013, **117**, 5568–5577.
- 150 J. Højberg, K. B. Knudsen, J. Hjelm and T. Vegge, *ECS Electrochem. Lett.*, 2015, **4**, A63–A66.
- 151 J. Liu, R. Younesi, T. Gustafsson, K. Edström and J. Zhu, *Nano Energy*, 2014, **10**, 19–27.
- 152 D. Aurbach, M. Daroux, P. Faguy and E. Yeager, *J. Electroanal. Chem. Interfacial Electrochem.*, 1991, **297**, 225–244.
- 153 W. Xu, J. Xiao, D. Wang, J. Zhang and J.-G. Zhang, *J. Electrochem. Soc.*, 2010, **157**, A219–A224.
- 154 G. A. Elia, J.-B. Park, Y.-K. Sun, B. Scrosati and J. Hassoun, *ChemElectroChem*, 2014, **1**, 47–50.
- 155 R. Younesi, M. Hahlin, M. Roberts and K. Edström, *J. Power Sources*, 2013, **225**, 40–45.
- 156 R. Younesi, S. Urbonaitė, K. Edström and M. Hahlin, *J. Phys. Chem. C*, 2012, **116**, 20673–20680.
- 157 G. M. Veith, J. Nanda, L. H. Delmau and N. J. Dudney, *J. Phys. Chem. Lett.*, 2012, **3**, 1242–1247.
- 158 P. Du, J. Lu, K. C. Lau, X. Luo, J. Bareno, X. Zhang, Y. Ren, Z. Zhang, L. A. Curtiss, Y.-K. Sun and K. Amine, *Phys. Chem. Chem. Phys.*, 2013, **15**, 5572–5581.
- 159 E. Nasybulin, W. Xu, M. H. Engelhard, Z. Nie, S. D. Burton, L. Cosimbescu, M. E. Gross and J.-G. Zhang, *J. Phys. Chem. C*, 2013, **117**, 2635–2645.
- 160 N. K. Karan, M. Balasubramanian, T. T. Fister, A. K. Burrell and P. Du, *J. Phys. Chem. C*, 2012, **116**, 18132–18138.
- 161 R. Younesi, M. Hahlin, F. Björefors, P. Johansson and K. Edström, *Chem. Mater.*, 2013, **25**, 77–84.
- 162 D. Chalasani and B. L. Lucht, *ECS Electrochem. Lett.*, 2012, **1**, A38–A42.
- 163 G. M. Veith, N. J. Dudney, J. Howe and J. Nanda, *J. Phys. Chem. C*, 2011, **115**, 14325–14333.
- 164 D. Sharon, V. Etacheri, A. Garsuch, M. Afri, A. A. Frimer and D. Aurbach, *J. Phys. Chem. Lett.*, 2012, **4**, 127–131.



- 165 B. D. McCloskey, A. Valery, A. C. Luntz, S. R. Gowda, G. M. Wallraff, J. M. Garcia, T. Mori and L. E. Krupp, *J. Phys. Chem. Lett.*, 2013, **4**, 2989–2993.
- 166 W. Xu, J. Hu, M. H. Engelhard, S. A. Towne, J. S. Hardy, J. Xiao, J. Feng, M. Y. Hu, J. Zhang, F. Ding, M. E. Gross and J.-G. Zhang, *J. Power Sources*, 2012, **215**, 240–247.
- 167 I. Gunasekara, S. Mukerjee, E. J. Plichta, M. A. Hendrickson and K. M. Abraham, *J. Electrochem. Soc.*, 2014, **161**, A381–A392.
- 168 R. Younesi, M. Hahlin, M. Treskow, J. Scheers, P. Johansson and K. Edström, *J. Phys. Chem. C*, 2012, **116**, 18597–18604.
- 169 R. Younesi, M. Hahlin and K. Edström, *ACS Appl. Mater. Interfaces*, 2013, **5**, 1333–1341.
- 170 S. Hyoung Oh, T. Yim, E. Pomerantseva and L. F. Nazar, *Electrochem. Solid-State Lett.*, 2011, **14**, A185–A188.
- 171 K. C. Lau, J. Lu, J. Low, D. Peng, H. Wu, H. M. Albishri, D. A. Al-Hady, L. A. Curtiss and K. Amine, *Energy Technol.*, 2014, **2**, 348–354.
- 172 B. D. McCloskey, D. S. Bethune, R. M. Shelby, T. Mori, R. Scheffler, A. Speidel, M. Sherwood and A. C. Luntz, *J. Phys. Chem. Lett.*, 2012, **3**, 3043–3047.
- 173 Z. Peng, S. A. Freunberger, L. J. Hardwick, Y. Chen, V. Giordani, F. Bardé, P. Novák, D. Graham, J.-M. Tarascon and P. G. Bruce, *Angew. Chem., Int. Ed.*, 2011, **50**, 6351–6355.
- 174 E. Yoo and H. Zhou, *ACS Nano*, 2011, **5**, 3020–3026.
- 175 F. Li, T. Zhang, Y. Yamada, A. Yamada and H. Zhou, *Adv. Energy Mater.*, 2013, **3**, 532–538.
- 176 Y. Liu, L. M. Suo, H. Lin, W. Yang, Y. Fang, X. Liu, D. Wang, Y.-S. Hu, W. Han and L. Chen, *J. Mater. Chem. A*, 2014, **2**, 9020–9024.
- 177 L. Cheng, R. S. Assary, X. Qu, A. Jain, S. P. Ong, N. N. Rajput, K. Persson and L. A. Curtiss, *J. Phys. Chem. Lett.*, 2015, **6**, 283–291.
- 178 Y. V. Mikhaylik, *US Pat.*, US7354680 B2, 2008.
- 179 L. J. Krause, W. Lamanna, J. Summerfield, M. Engle, G. Korba, R. Loch and R. Atanasoski, *J. Power Sources*, 1997, **68**, 320–325.
- 180 D.-J. Lee, M. Agostini, J.-W. Park, Y.-K. Sun, J. Hassoun and B. Scrosati, *ChemSusChem*, 2013, **6**, 2245–2248.
- 181 K. M. Abraham, Z. Jiang and B. Carroll, *Chem. Mater.*, 1997, **9**, 1978–1988.
- 182 M. Ue, *J. Electrochem. Soc.*, 1997, **144**, 2684–2688.
- 183 W. A. Henderson, *J. Phys. Chem. B*, 2006, **110**, 13177–13183.
- 184 K. Xu and C. A. Angell, *J. Electrochem. Soc.*, 2002, **149**, A920–A926.
- 185 R. Demir-Cakan, M. Morcrette, Gangulibabu, A. Gueguen, R. Dedryvere and J.-M. Tarascon, *Energy Environ. Sci.*, 2013, **6**, 176–182.
- 186 M. Rohde, P. Eiden, V. Leppert, M. Schmidt, A. Garsuch, G. Semrau and I. Krossing, *ChemPhysChem*, 2015, **16**, 666–675.
- 187 J. S. Park, D. J. Kim, J. W. Park, H. S. Ryu, K. W. Kim, G. X. Wang and H. J. Ahn, *J. Nanosci. Nanotechnol.*, 2012, **12**, 5794–5798.
- 188 S. Xin, L. Gu, N.-H. Zhao, Y.-X. Yin, L.-J. Zhou, Y.-G. Guo and L.-J. Wan, *J. Am. Chem. Soc.*, 2012, **134**, 18510–18513.
- 189 S. Kim, Y. Jung and S.-J. Park, *Electrochim. Acta*, 2007, **52**, 2116–2122.
- 190 J. Gao, M. A. Lowe, Y. Kiya and H. D. Abruña, *J. Phys. Chem. C*, 2011, **115**, 25132–25137.
- 191 K. Ueno, J.-W. Park, A. Yamazaki, T. Mandai, N. Tachikawa, K. Dokko and M. Watanabe, *J. Phys. Chem. C*, 2013, **117**, 20509–20516.
- 192 V. Kolosnitsyn, E. Kuzmina and E. Karaseva, *ECS Trans.*, 2009, **19**, 25–30.
- 193 D.-R. Chang, S.-H. Lee, S.-W. Kim and H.-T. Kim, *J. Power Sources*, 2002, **112**, 452–460.
- 194 C. Barchasz, F. Mesguich, J. Dijon, J.-C. Leprêtre, S. Patoux and F. Alloin, *J. Power Sources*, 2012, **211**, 19–26.
- 195 C. Barchasz, J.-C. Leprêtre, S. Patoux and F. Alloin, *J. Electrochem. Soc.*, 2013, **160**, A430–A436.
- 196 D. Zheng, X. Zhang, C. Li, M. E. McKinnon, R. G. Sadok, D. Qu, X. Yu, H.-S. Lee, X.-Q. Yang and D. Qu, *J. Electrochem. Soc.*, 2015, **162**, A203–A206.
- 197 E. S. Shin, K. Kim, S. H. Oh and W. Il Cho, *Chem. Commun.*, 2013, **49**, 2004–2006.
- 198 M. Hagen, S. Dörfler, P. Fanz, T. Berger, R. Speck, J. Tübke, H. Althues, M. J. Hoffmann, C. Scherr and S. Kaskel, *J. Power Sources*, 2013, **224**, 260–268.

